



Study of Some Properties of PbI₂ Deposited on Porous Silicon Using Thermal Evaporation Technique for Many Applications

Suha G. Ali*, Mohammed S. Mohammed, Fatima I. Sultan

Department of Applied Sciences, University of Technology – Iraq

Article information

Article history:

Received: December, 27, 2021

Accepted: April, 25, 2022

Available online: September, 10, 2022

Keywords:

Lead iodide,
Porous silicon,
Thermal evaporation,
X-ray diffraction

*Corresponding Author:

Suha G. Ali

as.18.05@grad.uotechnology.edu.iq

Abstract

The present work is a study of some properties of PbI₂ deposited on porous silicon (n-PSi) by using the thermal evaporation technique. X-ray diffraction, scanning electron microscopy, UV–Vis spectrophotometer, and FTIR analysis were used to characterize the structural, optical, and morphological properties of n-Psi. X-ray diffraction showed that the PbI₂ film has a hexagonal polycrystalline structure, while FE-SEM images showed porous silicone in Photoelectrochemical etching, the pore distribution is irregular and the pore refers to the increased surface area of the silicon. SEM images of pbI₂ film showed that particles were scattered and resembled gravel in size. The estimated optical energy value of thin films of PbI₂ was 2.6 eV. PbI₂ film has lower transmittance values at short wavelengths, but as the wavelength increases, the transmittance values gradually increased. The greatest transmittance value was 0.88. From FTIR analysis, chemical bonds were determined between porous silicon and PbI₂.

DOI: [10.53293/jasn.2022.4563.1126](https://doi.org/10.53293/jasn.2022.4563.1126), Department of Applied Sciences, University of Technology

This is an open access article under the CC BY 4.0 License.

1. Introduction

Lead Iodide (pbI₂) has emerged as a promising material with broad technical applications, including Perovskite photovoltaic solar cells, X-ray, and γ -ray detectors at room temperature [1-6]. Lead-iodide is an important ingredient in the fabrication of solar perovskite cells, which have been extensively explored by numerous researchers across the world and have recently achieved a Power Conversion Efficiency (PCE) of more than 20% [4]. Lead iodide is a semi-conductive type P with a high energy gap of 2.3-2.6 eV depending on the deposition process, and a high atomic number with iodine having atomic number = 82 and lead atomic number = 52, making it useful as an ionizing radiation detector [3], it also can be utilized in medical imaging, nuclear detection and photosensitivity semiconductor metal applications [7]. Generally, PbI₂ can be crystallized by a hexagonal lattice layered form. Its hexagonal closed-pack (HCP) crystal is made up of covalently bound layers of I–Pb–I that are piled on top of one another by weak van der Waals bonds perpendicular to the crystal c-axis [001]. The anisotropic features of pbI₂ crystals are due to this layered structure, which may lead to the formation of numerous polytypic structural changes. [8]. Porous silicon (PS) has recently been a matter of significant investigation, owing to its photoluminescence features and possible uses in photovoltaic devices, chemical sensors, and biological sensors [9, 10]. The idea of etching silicon surfaces has gained a lot of importance in semiconductors and solar cells since it helps to improve and produce devices that have a wide range of applications. The etching process has progressed to nanotechnology, where the material acquires new properties

as it reaches atomic dimensions and is governed by quantum rather than classical rules [11]. Porous silicon (PSi) is made up of a network of silicon wires and voids that are nanoscale in size. It is made in a variety of ways, including photoelectrochemical etching of the surface of crystalline silicon in an aqueous solution of (HF)acid, with carefully controlling the preparation conditions (etching time - slice specifications - acid concentration and current density) to obtain a suitable crystal structure from porous silicon with various layers of porosity [12,13]. This work aims to prepare lead iodide films deposited on porous silicon by a vacuum evaporation method, it also studies some properties of this material to present preliminary results for a variety of applications. In (2018), Rana Kadhim Abid alnabia, Malek A.H. Muhi et al have prepared lead iodide that was applied to glass bases by a thermal evaporation process, they also studied optical and electrical properties. The film showed a hexagonal crystalline shape. The value of the energy gap for a sample of 200 nm thickness is 2.9051 eV, the intensity is at the plane (003), it equals 12.5 nm. The electrical properties were studied for the measurements of electrical conductivity, mobility, carrier concentration, and finally the Hall coefficient. The results are $(1.038 \times 10^{-5}$, $0.6727 \times 10^{+2}$, 1.009×10^{12} and 2.631×10^6), respectively [14]. K. I. HASSOON, M. S. MOHAMMED, et al, (2019) prepared porous PbI₂ thin films to be investigated. Various thicknesses of lead iodide thin films were prepared by the fast thermal evaporation technique (TET). Scherrer's analysis indicated that grain size extends from about 8 to 18 nm. Scan electron microscopy (SEM) revealed high porosity of pbI₂thin films. UV-Vis spectroscopy and diffuse reflectivity were used to calculate the optical band gap. The two methods indicated that the PbI₂ prepared by TET has a direct optical band gap (about 2.5 eV) with the Urbach tail width of the order 0.76 eV. [15]. Kawther A. Khalaph et al. (2020), studied the character of preparation, and structural and optical properties of pbI₂ materials. Structural properties are included in the investigation of measurements. X-ray Diffraction (XRD) revealed that the pbI₂thin film had a hexagonal defect and diffusion crystalline structure with constant lattice ($a=4.67\text{\AA}$, $c=7.52\text{\AA}$). Scan Electron Microscopy (SEM) images referred to the formation of rods and sheet configurations. The peak at a frequency of 1627 refers to Fourier Transform Infrared spectroscopy (FTIR), the band Pb-I, and Atomic Force Microscopy (AFM). Lead Iodide (pbI₂) film possesses the characteristics of full surface coverage and is pinhole-free on the substrates. UV- Vis tests of thin-film samples deposited on glass substrates were used to examine and evaluate optical parameters such as absorption, transmittance, and the energy gap ($E_g = 2.3\text{ eV}$) [16].

2. Experimental Procedures

2.1. Preparation of Porous Silicon

The substrate was a crystalline wafer of n-type Silicon with a resistivity of $(5)\ \Omega\cdot\text{cm}$, a thickness of 500 m, and an orientation of 100. The substrates were cut with $(1.5 \times 1.5\text{cm}^2)$ areas. After chemical treatment, $0.1\ \mu\text{m}$ thick Al layers were formed on the backsides of the wafer using an evaporation method. Photoelectrochemical etching was then carried out at room temperature by employing a platinum electrode in a mixture (1:1) of HF (45%) and Ethanol (99.99%). The light source was a Halogen lamp with a light intensity of $20\text{mW}/\text{cm}^2$ to ensure homogeneity of the etch layer, current of $14\text{mA}/\text{cm}^2$ was applied for 8 minutes as shown in Figure 1. The etched area was (0.785 cm^2) as shown in Figure 2.

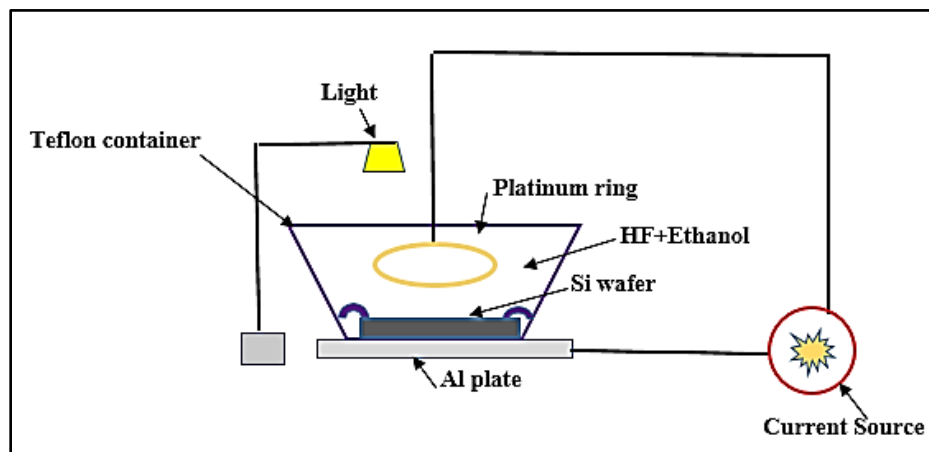


Figure 1: The schematic diagram of the Photoelectrochemical etching method.

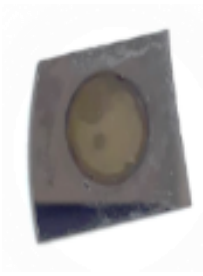


Figure 2: Porous silicon sample.

2.2. Preparation of PbI₂ thin Film

PbI₂ films of 200 nm thickness were deposited on a cleaned glass and PSi substrate by the thermal evaporation method at a 10⁻⁵ Torr vacuum using a high vacuum coating apparatus (Edwards type E306A). The distance between the source and the substrate was roughly 18 cm inside the vacuum chamber, where a molybdenum boat was utilized to transport PbI₂ powder. Figure 3 a & b shows the thermal evaporation procedure and the PbI₂ thin film after it has been deposited on the PSi substrate, while Figure 4 shows the cross-section image of the heterojunction that has been prepared.

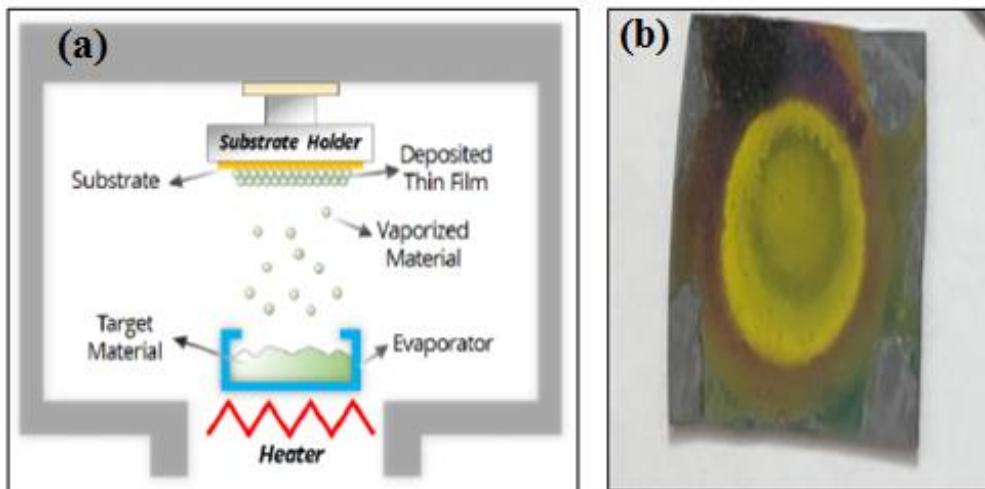


Figure 3: (a): Scheme of thermal evaporation method, and (b): PbI₂ thin film on PSi substrate.

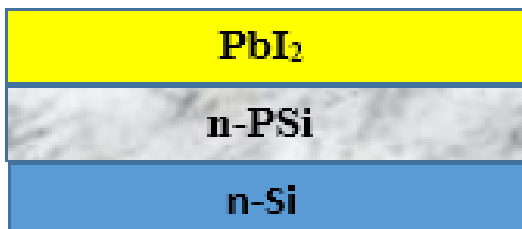


Figure 4: Across-section view of the prepared n-Si/n-PSi/PbI₂ heterojunction.

3. Characterization

PbI₂ and PSi film were characterized by utilizing characterization techniques, namely: X-ray diffraction (XRD), Scanning electron microscopy (SEM), UV-Vis, and Fourier transform infrared spectroscopy (FTIR).

4. Results and Discussion

Figure 5 shows X-ray diffraction of crystalline Si and n-PSi materials. Blue plots for n-Si and red drawings for PSi were produced by anodization with a current density of 14 mA/cm^2 and an etching period of 8 minutes. When compared to the peak of n-type porous silicon (n-PSi), the crystalline Si peak has a higher intensity value. Even after the etching procedure, the etched silicon retains its single crystal structure, but due to strain, it slightly moved to a small diffraction angle (2θ 69.428° and 69.381°), orientated exclusively along the 400 direction, resulting in a modest expansion in the lattice parameter [17, 18].

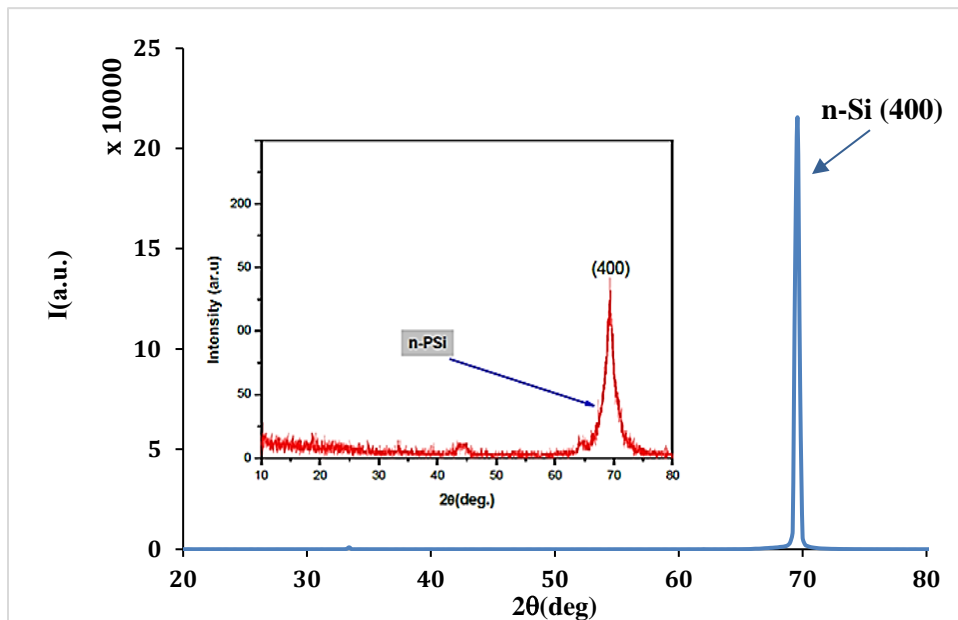


Fig.5. XRD spectra of n-type Silicon (n-Si) and porous silicon (n-PSi) (prepared with 14 mA/cm^2 etching current density at etching times 8 min).

The Cu-K target with wavelength 1.54060 \AA was used to achieve X-ray diffraction of PbI_2 film that was produced on PSi substrate (using XRD Analysis XRD- 6000). Figure 6 reveals the principle diffraction peaks at corresponding planes 001, 101, 002, 202, 003, 210, and 004 at the diffraction angles 12.73° , 23.98° , 25.58° , $28.38.65^\circ$, 39.7 , and 52.13° , respectively.

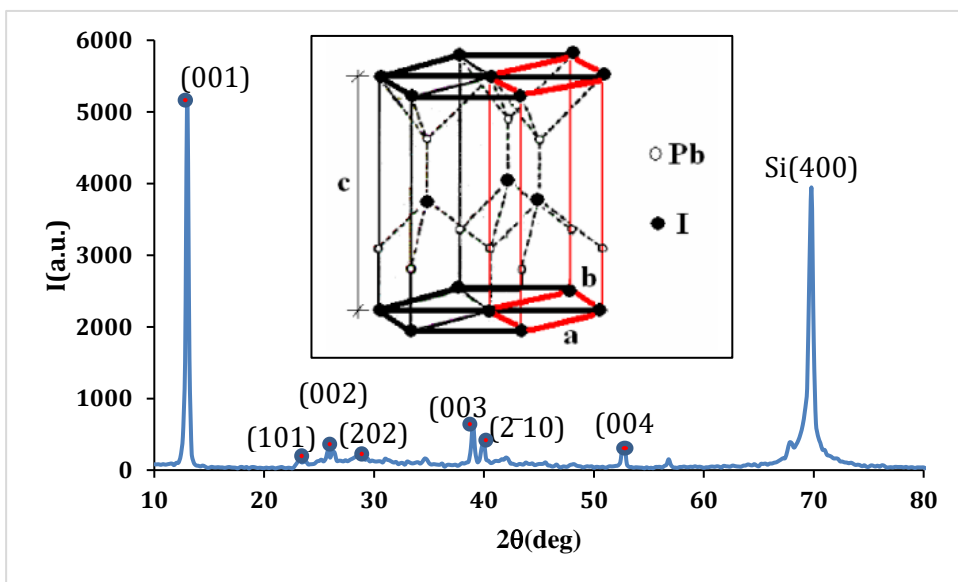


Figure 6: XRD pattern for PbI_2 thin film prepared by vacuum thermal evaporation method.

Similarly, the figure reveals the sharp and narrow peak at the angle of 69.8° for the porous silicon layer with orientation (004). PbI_2 thin film is polycrystalline and has a hexagonal structure, it was indicated in the JCDPS card about [14]. Scherer's Formula (Eq.1) was then used to calculate the average crystalline size that was around (18.28) nm [14-20] when θ , and β in radian angle, and k is a shape factor that equals 0.9.

$$D = \frac{k \lambda}{\beta \cos \theta} \quad (1)$$

D : crystalline size, (λ): wavelength for x-ray (1.5406\AA), β : is the full Width at half maximum, and θ : is a degree of diffraction [21]. Figure 7a shows the SEM image of the PSi surface prepared at a current density of 14 mA/cm^2 for an 8-minute etching duration. The bright parts in both photos indicate Si structures, while the dark regions represent pores. The sponge-like structure of the porous silicon layer is readily visible in the images. Pores of varying sizes and spherical forms exist in the prepared layer. Pore diameter ranges from 100 to 200 nanometers. Figure 7b shows the SEM images of PbI_2 film on porous silicon deposited by thermal evaporation, where it was observed that the particles scattered on the surface in a heterogeneous manner, mimicking gravel forms, resembling gravel shapes, and their different sizes do not exceed 100 nanometers.

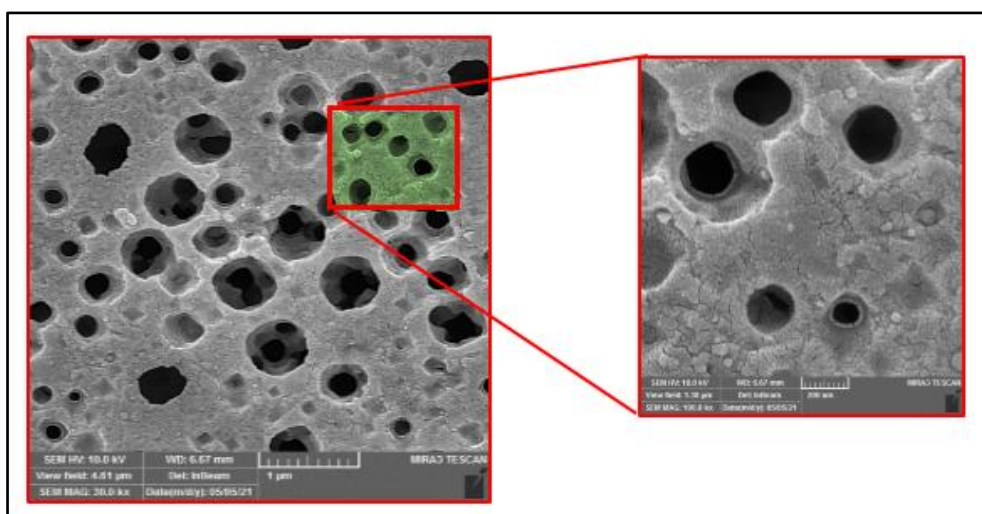


Fig.7a. SEM images of porous silicon samples were prepared with an etching time of (8mins.) at a current density of 14 mA/cm^2 .

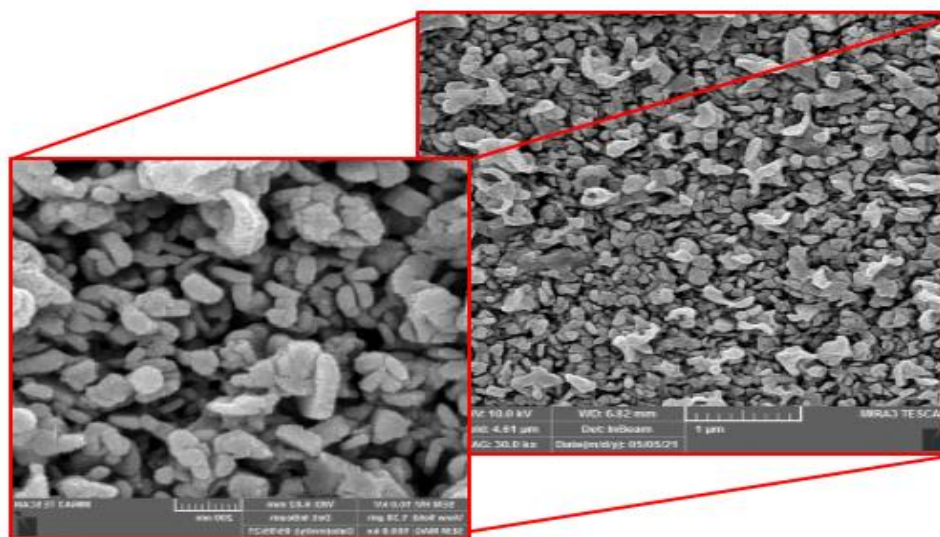


Figure7b. SEM images for PbI_2 thin film surfaces on porous silicon.

The optical properties were recorded by using a UV-Vis spectrophotometer (Metertech SP8001). Figure 8 shows the transmission spectra of PbI₂ films deposited on a glass substrate using thermal evaporation as a function of wavelength (200-1000) nm. The film's structure, preparation, film thickness, and deposition circumstances all have a significant impact on transmission. PbI₂ film has lower transmittance values at shorter wavelengths, but as the wavelength increases, the transmittance values gradually increase. The greatest transmittance value was 0.88, which is ideal for optoelectronic devices, particularly solar cell window layers. Furthermore, a dramatic drop at the band's edge refers to PbI₂ film crystallinity, which is consistent with XRD data.

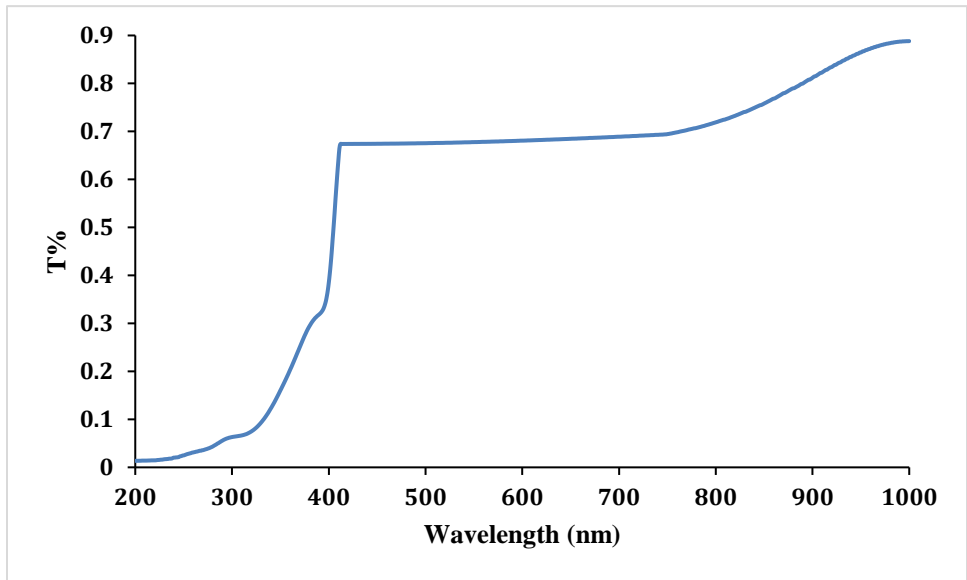


Figure 8: The transmission spectrum of PbI₂ films deposited on glass substrate by thermal evaporation

Tauc plot was used to analyze the optical band gap. Figure 9 depicts a linear relationship between $(\alpha h\nu)^2$ and photon energy. This behavior indicates that a direct permitted transition is possible in the PbI₂ film. From the linear part of the curve to the photon energy axis, the optical band gap can be extracted [15]. For PbI₂ thin film, the extrapolation yielded a band gap of 2.65 eV. The energy gap was calculated by using Eq. (2):

$$(\alpha h\nu)^2 = B(h\nu - E_g)^n \tag{2}$$

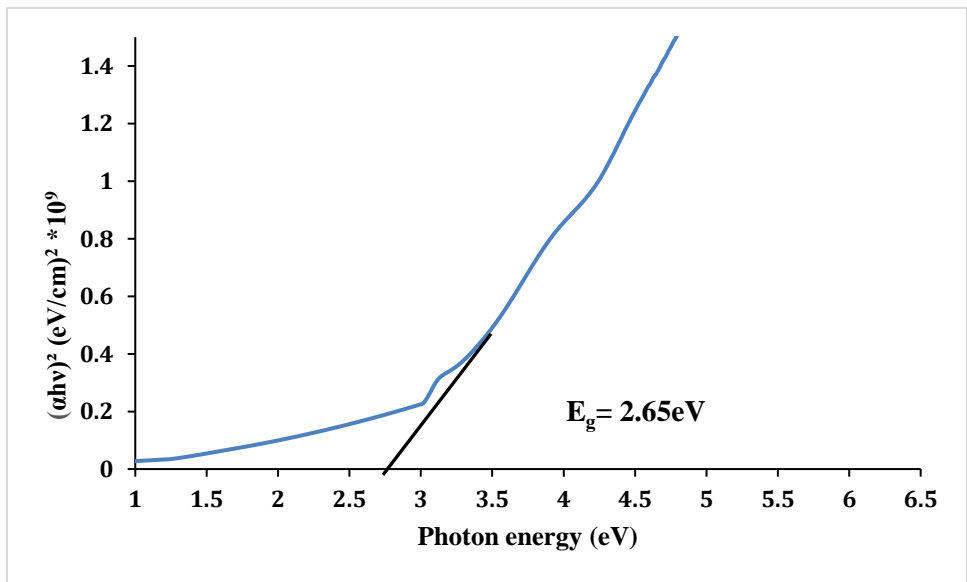


Figure 9: $(\alpha h\nu)^2$ vs. $(h\nu)$ plot for PbI₂ thinfilm.

FTIR technique is a potent tool for determining the chemical species present in the substance. This approach measures how much radiation can be absorbed by chemical bonds in the substance as the wavelength of the radiation changes in the infrared range. Different chemical bonds absorb different frequencies of radiation [22]. The best way to determine the chemical composition of the PSi surface is to use Fourier Transform Infrared (FTIR) spectroscopy. Because PSi has a substantially bigger specific area than bulk Si, the FTIR signal is larger and easier. The surface of the manufactured PSi layer oxidizes spontaneously after a few hours in ambient air [23]. For original impurities such as hydrogen and fluorine, which are residuals from the electrolyte, the pore surface has a high density of dangling Si bonds. Figure 10a shows that the FTIR spectra can be measured from samples at current density (14 mA/cm^2), and etching time (8) minutes. The peaks at around 617 cm^{-1} , 663 cm^{-1} , and 891 cm^{-1} are from Si-Si, Si-H, and Si-O, respectively. The transmittance peak at $1423\text{-}1465 \text{ cm}^{-1}$ and 1519 cm^{-1} is due to C-H. The peak at 1708 and 2380 cm^{-1} is due to C-O, and peaks at 3614 and 3745 cm^{-1} are due to O-H and Si-OH [24-28]. Figure 10b shows IR spectra of the PbI₂ sample that was deposited on the PSi substrate. The peak at frequency 1627 is referred to as the band Pb-I [29]. The peaks around 3412 and 3383 cm^{-1} are due to asymmetric and symmetric stretching vibrations of the Pb-I cluster [30]. It can be noted that the appearance of weak peaks of PbI₂, which perhaps can be attributed to the PSi substrate.

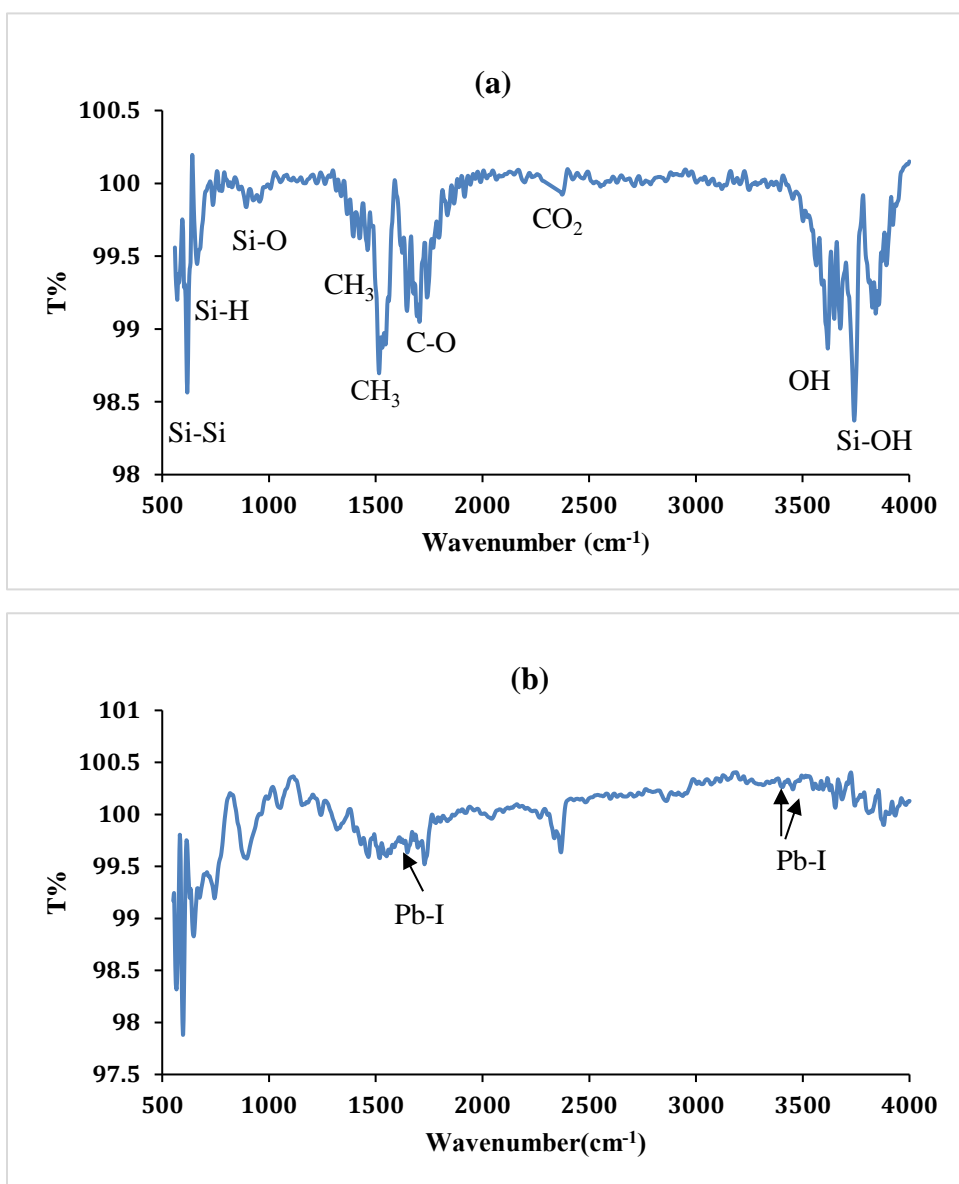


Figure 10: FTIR spectra (a): n-PSi layer and (b) PbI₂/PSi Heterojunction.

4. Conclusions

We have prepared and characterized the nanocrystalline porous silicon layer and PbI₂ thin film by thermal evaporation technique to study some of its properties. X-ray diffraction showed that the PbI₂ film has a hexagonal polycrystalline structure. The band gap energy for PbI₂ was estimated to be 2.6 eV. FE-SEM images showed porous silicone via using the photoelectrochemical etching method, the pore distribution is irregular. SEM images of PbI₂ film revealed that particles were scattered and resembled gravel in size. The results indicated that PbI₂ can be used in physical applications such as solar cells.

Acknowledgment

The authors thank the Department of Laser Science and Technology, University of Technology for funding the activities presented in this study.

Conflicts of Interest

There are no conflicts of interest.

References

- [1] D. S. Ahlawat, "Study of Band Gap Energy and Thermal Properties of PbI₂ by Photoacoustic Spectroscopy," *Mod. Phys. Lett. B*, vol. 26, no. 16, pp. 1250098, 2012.
- [2] A. M. Jafar, M. H. Suhyl, and F. I. Mustafa, "Organolead Iodide Perovskite Solar," vol.2, no. 6, pp. 81–87, 2016.
- [3] Aqel Mashot Jafar, Mahdi, Falah Mustafa Al-Attar, & M. K. K. "Organolead Halide Perovskite Solar Cells," In 32st European Photovoltaic Solar Energy Conference And Exhibition, pp. 1296–1302, (2016).
- [4] Z. Shi And A. H. Jayatissa, "Perovskites-Based Solar Cells: A Review of Recent Progress,materials and processing methods," *Materials*, vol. 11, no. 5, 2018.
- [5] M. H. Suhail and A. M. Jafar, "Fabrication and Characterization of Organolead Halide Peroviske Solar," vol. 98, pp. 42709–42713, 2016.
- [6] W. Wang et al., "Highly Sensitive Low-Bandgap Perovskite Photodetectors with Response from Ultraviolet to the Near-Infrared Region," *Adv. Funct. Mater.*, vol. 27, no. 42, 2017.
- [7] Acuña1, B KrishnanSSHaji, S Sepúlveda a nd J L Menchaca"Growth and Properties of Lead Iodide thin films by spin coating", Indian Academy of Sciences (2016).
- [8] Condeles J. F. and Ando R. A., "Optical and Structural Properties Of Pbi₂ Thin Films", *J. Mater. Sci.*, vol. 43 525, 2007.
- [9] M. S. Mohammed, R. A. Shlaga "Reflectivity effect of the PS on solar cell efficiency" IOP Conf. Series: Journal of Physics: Conf. Series 1032, 012027, (2018).
- [10] J. Torres, H. M Martinez, J. E. Alfonso and L. D. Lopez C, "Optoelectronic study in porous silicon thin films", *Microelectronics Journal*, vol. 39, pp.482-484, 2008.
- [11] Mark Ratner, Dan Ratner, Nanotechnology Gentle Introduction, Harvard University, Brown University (2002).
- [12] Narayanan, Purnima. Photoelectrochemical Etching of Isolated, High Aspect Ratio Microstructures in n-Type Silicon (100). MSc.Thesis, Department of Chemical Engineering by, University of Mumbai, (2011).
- [13] Adawiya J Haider, Jassim M Abass,Preparation and Characterization of Porous Silicon Prepared by Electrochemical Etching, *Engineering and Technology Journal*, vol. 32, no. 4, pp. 623-628, 2014.
- [14] RanaKadhimAbidalnabia),Malek A.H. Muhi, Aus A. Najim,"Structure and optical properties of pbI2 thin film by thermal evaporation technique", *J. of University of Anbar for Pure Science*, vol.12, no.2, 2018.
- [15] K. I. Hassoon, M. S. Mohammed, G. D. Salman "Characterization of Pbi2 Thin Films Prepared By Fast Vacuum Thermal Evaporation", *Digest Journal Of Nanomaterials And Biostructures*, vol. 14, no. 2, 2019.
- [16] Kawther A. Khalaph1, a, Zainab J. Shanan1,b, AqelMashotJafar, Falah Mustafa Al-Attar2, "Structural and Optical Properties of PbI2 Thin Films to Fabricate Perovskite Solar Cells", *Materials Engineering and Science* (2020)
- [17] M. G. Yousif, "Solid State Physics", 2nd Edition, Baghdad University, Arabic version, (1989).
- [18] Ibrahim r. agoolet al," improving the photoresponse of porous silicon for solar cell applications by embedding of cdte nanoparticles", *Surface Review and Letters*, vol. 25, no. 2, pp. 1850012, 2018.
- [19] J. F. Condeles, R. A. Ando, M. Mulato"Optical and structural properties of PbI2 thin films", *J Mater Sci* (2008).

- [20] Mohammed S. Mohammed, Ghassaq D. Salman*, and Khaleel I. Hassoon "Growth and Characterizes of PbI₂ Films by Vacuum Evaporation Method", *Al-Mustansiriyah Journal of Science*, vol. 30, no. 2, 2019.
- [21] T. Hamatani, Y. Shirahata, Y. Ohishi, M. Fukaya, T. Oku, Arsenic and chlorine codoping to CH₃NH₃PbI₃ perovskite solar cells, *Adv. Mater. Phys. Chem.*, vol. 07, no. 01, pp. 1–10, 2017.
- [22] Raheem G. Kadhim 1, Raid A. Ismail and Wasna'a M. Abdulridha, "Structural, Morphological, Chemical and Optical Properties of Porous Silicon Prepared by Electrochemical Etching", *Int. J. Thin. Fil. Sci. Tec.*, vol. 4, no. 3, pp. 199-203, 2015.
- [23] U. M. Nayef, "Fabrication and Characteristics of Porous Silicon for Photoconversion", *International Journal of Basic and Applied Sciences IJBAS-IJENS*, vol. 13, no. 02, 2013.
- [24] J. Michael Sailor, "Porous Silicon in Practice: Preparation, Characterization and Applications," Wiley-VCH Verlag & Co. KGaA, (2012).
- [25] O. Bisi, Stefano Ossicini, L. Pavesi, *Surface Science Reports*, vol. 38, pp. 1-126, 2000.
- [26] S. Basu, "Crystalline Silicon - Properties and Uses", InTech, (2011).
- [27] B. K. Mohamid, U. M. Nayef, Z. F. Kadem, *Journal of Al-Nahrain University*, 145-115, (2013).
- [28] Ahmed N. Abd " Improved photoresponse of porous silicon photodetectors by embedding CdS nanoparticles", *World Scientific News*, vol. 19, 2015.
- [29] Ahmed N. Abd, Nadir F. Habubi, Ali H. Reshak and Hazim L. Mansour "Enhancing the Electrical Properties of Porous Silicon Photodetector by Depositing MWCNTs", *International Journal of Nanoelectronics and Materials*, vol. 11, no. 3, 2018.
- [30] K. Kaviyarasu, D. Sajan, M.S. Selvakumar, S. Augustine Thomas, D. PremAnand, A facile hydrothermal route to synthesize novel PbI₂ nanorods, *J. Phys. Chem. Solids*, vol. 73, no. 11, pp. 1396–1400, 2012.