

Determination of Monomer Reactivity Ratios of Poly (Acrylonitrile – co – vinylacetate)

Tariq S.Najim
College of Scienc

Abdul Hussien K. Sharba
College of Scienc
University of Al-Mustansiryah

Nadia A. Butti
College of Scienc

(NJC)

(Received on 15/11/2006) (Accepted for publication on 22/8 /2007)

Abstract :

Copolymers of Acrylonitrile (AN) and Vinyl Acetate (VAc) were synthesized in dimethyl formamide (DMF) using benzoyl peroxide (BPO) as initiator at 75°C . The copolymers were analyzed by IR spectroscopy. The monomer reactivity ratios were determined by the methods of Fineman – Ross (F-R) and Kelen – TüdÖs (K-T) giving the results shown in the following table:-

$r_1(\text{AN})$				$r_2(\text{VAc})$			
F-R		K-T		F-R		K-T	
1 st	2 nd	1 st	2 nd	1 st	2 nd	1 st	2 nd
2.2347	2.5341	2.3889	2.7087	0.0303	0.002	0.1038	0.0719

الخلاصة

تم تحضير البوليمر المشترك للأكريلونيتريال (AN) و الفينيل أسيت (VAc) في مذيب ثنائي مثيل فورمايد (DMF) باستخدام بيروكسيد البنزويل كبادئ وبدرجة حرارة 75°C . تم تحليل البوليمر المشترك بواسطة مطيافية الأشعة تحت الحمراء .
الفعالية النسبية للمونمرات تم تحديدها بواسطة طريقة فنمان و روس (F-R) وطريقة كلين-ثيودوس (K-T) و النتائج موضحة في الجدول التالي :

$r_1(\text{AN})$				$r_2(\text{VAc})$			
F-R		K-T		F-R		K-T	
1 st	2 nd	1 st	2 nd	1 st	2 nd	1 st	2 nd
2.2347	2.5341	2.3889	2.7087	0.0303	0.002	0.1038	0.0719

Introduction :

Japan has recently been the leading contributor in the diversification of the production of modified acrylic fibers(1) More than 85% of acrylonitrile monomer must be incorporated into copolymer in order for it to be termed an acrylic fiber(2). Copolymerization of acrylonitrile with various comonomers produces specialty fibers for different applications. Methyl acrylate, methyl methacrylate and vinyl acetate are the commonly used "neutral" comonomers. They increase solubility and change the morphology of the fiber(3). The theory of radical copolymerization leads to the conclusion that the composition of the copolymer is determined by the reactivity ratios (r_1 and r_2) which reflect the inherent tendencies of a radical to react with its own monomer relative to the comonomer. copolymerizations are classified according to values of the product r_1r_2 . When $r_1r_2 = 0$, an alternating copolymer is produced, when $r_1r_2 = 1$, the copolymerization is said to be ideal, since $r_1 = \frac{1}{r_2}$, the copolymer is random.

Many methods have been used to estimate reactivity ratios of a large number of comonomers but the method of increasing application are those of Fineman- Ross and Kelen – TüdÖs (4). $^1\text{H-NMR}$, $^{13}\text{C-NMR}$ and FTIR methodologies are used to determine the copolymer composition(5).

The aim of the present work is to evaluate the reactivity ratios of comonomers using two methods, both of them depend on the absorption and absorptivity of certain group in the monomers and copolymers.

Experimental :

1- Materials and purification

Acrylonitrile (AN) (Aldrich) was washed with (10% NaOH) to remove inhibitors and then washed with distilled water to remove any trace of NaOH and finally distilled at reduced pressure. Vinyl acetate (VAc) was distilled before use. Dibenzoyl peroxide BPO (Aldrich) was purified by dissolving in small amounts of chloroform followed by precipitation with n - hexane.

2- Synthesis

For copolymerization, the AN and VAc in various proportions but with the total weight maintained at 4g and the initiator BPO being kept at concentration of (3×10^{-4} mol/L) were dissolved in 25 ml of DMF. The content of the flask was degassed with argon for at least 2 minutes and polymerization was carried out at 75°C for a period of 30 minutes. Each copolymer was

Results and Discussion

3-Determination of Molar Fractions (F)

The molar fractions of (AN) and (VAc) in poly (AN-co-VAc) were determined by two methods:-

precipitated by ethanol, washed repeatedly in methanol and dried. For the determination of reactivity ratio, the polymer conversions were always less than 5%. Homopolymers of AN and VAc were also prepared and their absorbances were measured using liquid cell with path length of 1cm. The IR spectra of copolymers and homopolymers were recorded by Pye Unicam (SP3-100 IR) as films on KBr window, figure (1).

a) The first method

This method depends on the absorbance of the recorded analytical absorption bands that is *CN* and *CO* for (AN) and (VAc) respectively, besides the molecular weights of the (AN) and (VAc) according to the following equations(6) :-

$$F_1 = \frac{ACN / M_1}{ACN / M_1 + Aco / M_2} \dots\dots(1)$$

$$F_2 = \frac{Aco / M_2}{Aco / M_2 + ACN / M_1} \dots\dots(2)$$

Where A is the absorbance of CN and CO at 2240, 1720 cm⁻¹ respectively. F1 and F2 are the molar fractions of (AN) and (VAc) in the

b) The second method

This method depends on the absorbance of the recorded analytical absorption bands for *CN* and *CO* for

$$F_1 / F_2 = (A_{CN} / A_{CO}) (\epsilon_{CO} / \epsilon_{CN}) \dots\dots(3)$$

copolymer respectively, M1 and M2 are the molecular weights of (AN) and (VAc) respectively.

(AN) and (VAc) respectively, besides the molar absorptivities of the *CN* and *CO* groups according to the following equation(7).

Where F_1 and F_2 are the molar fractions of (AN) and (VAc) in the copolymer, while ϵ_{CO} and ϵ_{CN} are the molar absorptivity of CN and CO respectively. The ϵ_{CN} and ϵ_{CO} were found to be 1.7543 and 3.2166 L.cm-

l.mol⁻¹ respectively. From the monomer feed ratio and the resultant copolymer composition, the reactivity ratios of (AN) and (VAc) were evaluated by Fineman – Ross and Kelen – TüdÖs equations that are:-

$$f(F-1)/F = r_1 \frac{f^2}{F} - r_2 \dots\dots\dots (4) \quad \text{Fineman - Ross}$$

$$\eta = (r_1 + r_2/\alpha)\zeta - \frac{r_2}{\alpha} \dots\dots\dots (5) \quad \text{Kelen - TüdÖs}$$

Where :

$$\eta = \frac{f(F-1)/F}{f^2/F + \alpha} \quad \zeta = \frac{f^2/F}{f^2/F + \alpha} \quad \alpha = \sqrt{(f^2/F)_{\max} (f^2/F)_{\min}}$$

A plot of $f(F-1)/F$ against f^2/F gives straight line, with slope = r_1 , and intercept = $-r_2$.

A plot of η against ζ gives straight line the slope = $r_1 + r_2/\alpha$ while the intercept = $-r_2/\alpha$ the results are presented in the following tables:-

%T

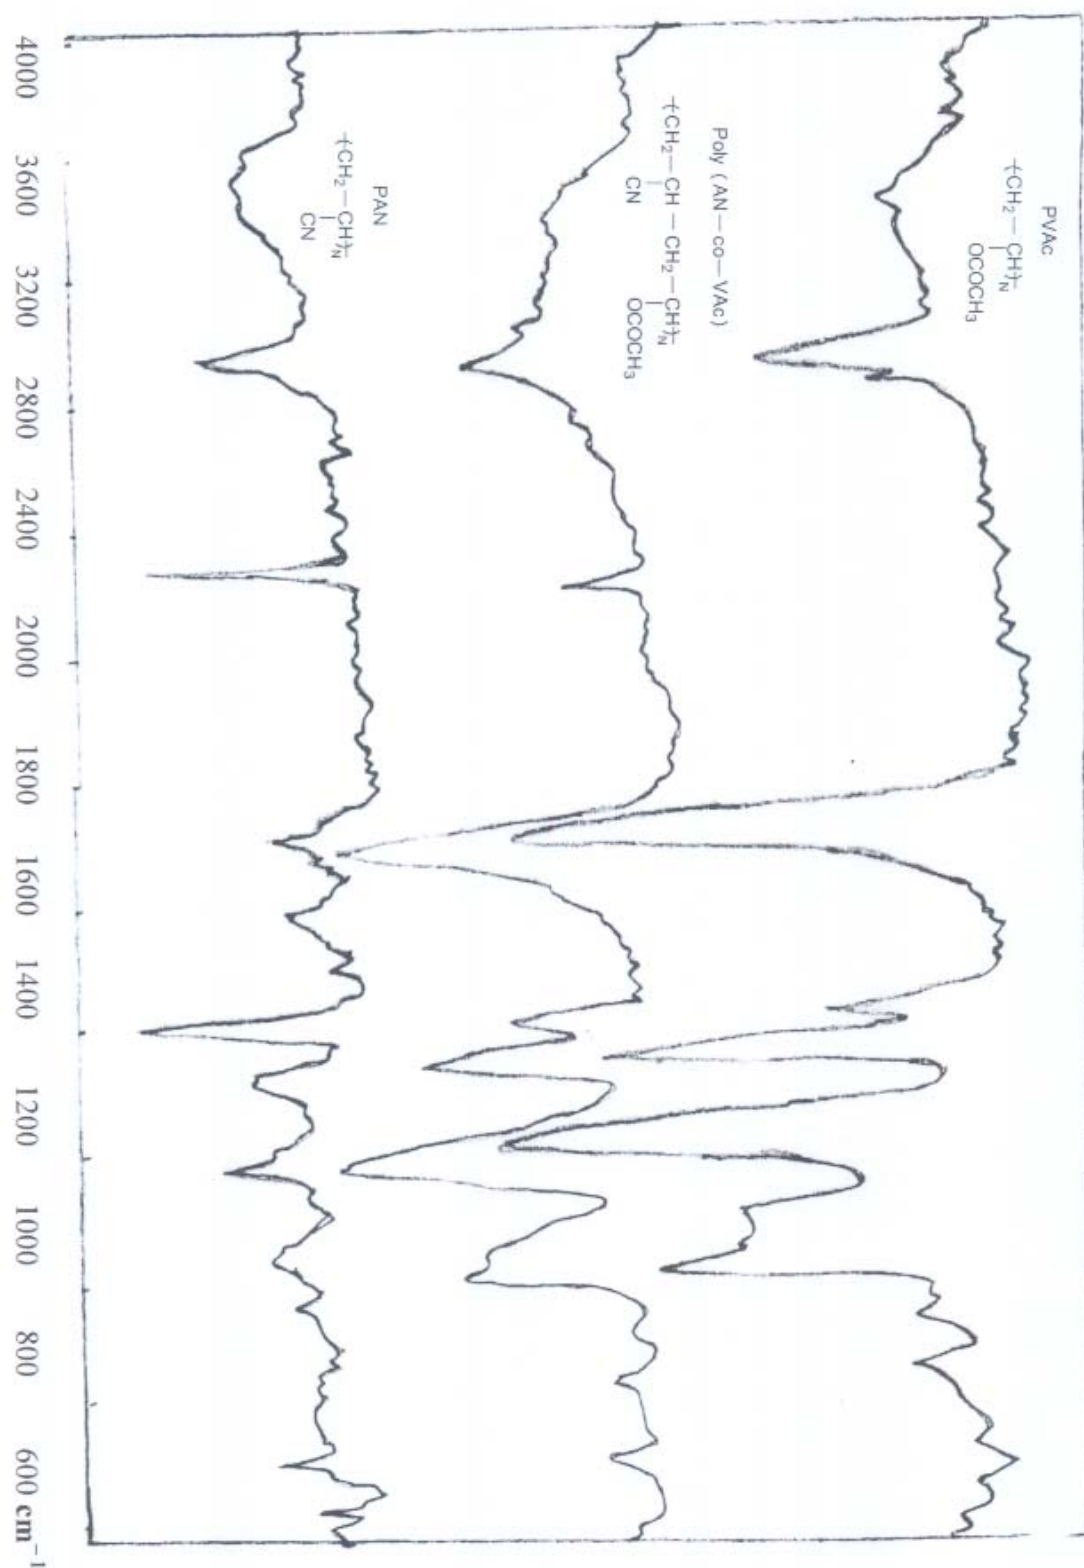


Fig (1) IR spectra of poly (AN - co - VAc), PAN and PVAc

Table (1) IR analysis data for determining the composition of poly (AN – co-VAc) prepared from various initial monomer mixture

Copolymer	Mole Fraction of Monomer in Feed		IR Absorbance		Mole Fraction of Monomer in Copolymer	
	f ₁ for AN	f ₂ for VAc	AN	VAc	F ₁ for AN	F ₂ for VAc
			CN	CO		
A ₁	0.8295	0.1704	0.94	0.13	0.9214	0.0785
A ₂	0.73	0.2699	1.33	0.31	0.87439	0.1256
A ₃	0.6187	0.38129	0.46	0.16	0.8234	0.1765
A ₄	0.4933	0.50669	0.378	0.16	0.7931	0.2068
A ₅	0.351	0.6489	0.183	0.14	0.67959	0.3204
A ₆	0.1881	0.8118	0.108	0.24	0.422	0.5779

The following table shows the values of r_1 and r_2 : -

Table (2) : copolymerization constants r_1 and r_2 for poly (AN-co-VAc)

(F-R) equation				(K-T) equation			
1 st		2nd		1st		2nd	
r ₁	r ₂	r ₁	r ₂	r ₁	r ₂	r ₁	r ₂
2.2347	0.0303	2.5341	0.002	2.3889	0.1038	2.7087	0.0719

From the values of r_1 and r_2 it seems that (AN) is more reactive than

(VAc) , where the macroradical prefers to add (AN) more than (VAc) .

Table (3) Fineman – Ross and Kelen – TüdÖs equations parameters of poly (AN – co- VAc) in DMF at 75°C when $\alpha_{1st} = 0.3852$ $\alpha_{2nd} = 0.3408$

Copoly- mer	$f=f_1/f_2$	$F=F_1/F_2$		F-R Equation parameters				K-T Equation parameters			
				f^2/F		$f(F-1)/F$		η		ξ	
		1 st	2 nd	1 st	2 nd	1 st	2 nd	1 st	2 nd	1 st	2 nd
A ₁	4.8679	11.7375	13.2576	2.0188	1.7873	4.4531	4.5007	1.8523	2.11489	0.8397	0.8398
A ₂	2.7047	6.9617	7.8663	1.0508	0.9299	2.3161	2.3608	1.6128	1.8578	0.7317	0.7318
A ₃	1.6226	4.6651	5.2713	0.5643	0.4994	1.2747	1.3147	1.34249	1.5647	0.5943	0.5943
A ₄	0.9735	3.8351	4.3316	0.2471	0.2187	0.7196	0.7487	1.138	1.3381	0.39079	0.3908
A ₅	0.5409	2.121	2.3966	0.1379	0.122	0.2858	0.3152	0.5463	0.681	0.2636	0.2636
A ₆	0.2317	0.7302	0.825	0.0735	0.065	-0.0856	-0.0491	-0.1866	-0.1209	0.1602	0.1601

The following figures show the Plots of equations for first and second method :
Fineman – Ross and Kelen – TüdÖs

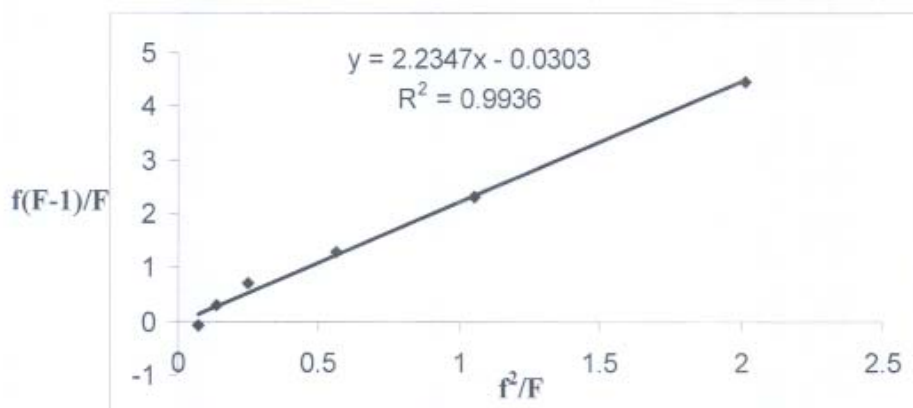


Fig (2) A plot of (F-R) (1st method) for the copolymer
(AN – co – VAc)

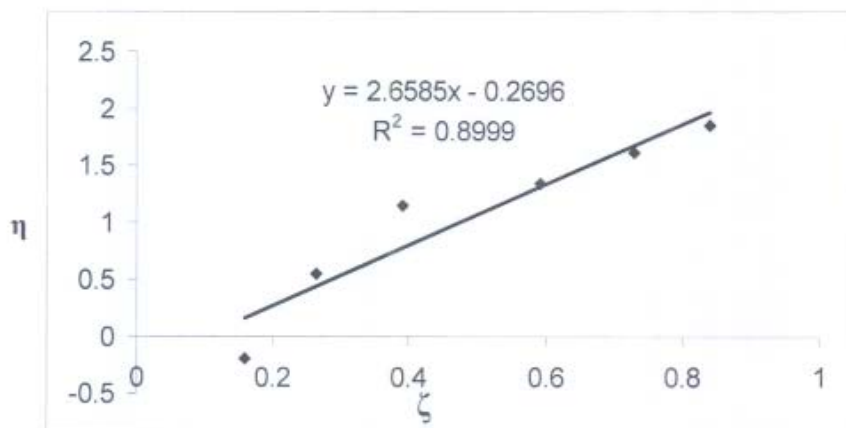


Fig (3) A plot of (K-T) (1st method) for the copolymer
(AN – co – VAc)

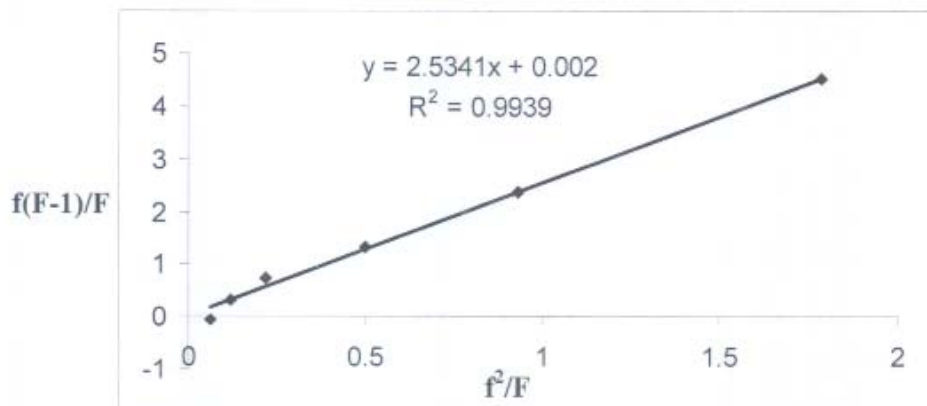


Fig (4) A plot of (F-R) (2nd method) for the copolymer
(AN – co – VAc)

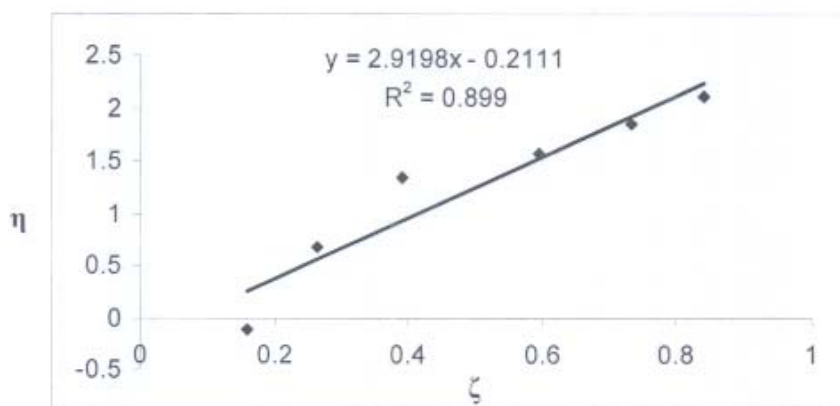


Fig (5) A plot of (K-T) (2nd method) for the copolymer (AN – co – VAc)

3-2 copolymerization behavior

We can predict the copolymer type (alternate, random or block) from

the product ($r_1 r_2$) The values of this product are summarized in table (4) :-

Table (4) the values of ($r_1 r_2$) for poly(AN-co-VAc)

$r_1 r_2$			
(F-R) equation		(K-T) equation	
1 st	2 nd	1 st	2 nd
0.0677	0.005	0.2479	0.1947

According to these values, the nature of the copolymer sequence of poly (AN-co-VAc) system is tending to alternate since the product $r_1 r_2$ closer to zero, so there is a greater tendency for (AN) and (VAc) to alternate in the copolymer poly (AN-co-VAc) due to big differences in polarity between the two monomers which leads to a transition state stabilized by resonance

which prefer to add either of the two monomers by the same preference.

Depending on the experimental values of r_{AN} and r_{VA} , the values of Q and e for each monomer were calculated and found as follows: for AN, $Q = 0.539$, $e = 1.67$, for VA, $Q = 0.0339$, $e = -0.189$ these values are in good agreement with values in literature(8). The copolymer

composition (F_1) vs initial composition (f_1) (fig 6), shows no

resemblance between the feed and the copolymer compositions. From the values of r_{AN} and r_{VA} one can deduce that AN is more reactive than VAc to go into copolymer.

This behavior can be explained on the basis that AN radical is more stable than VAc radical so the growing macroradical prefer to add to AN more than VAc.

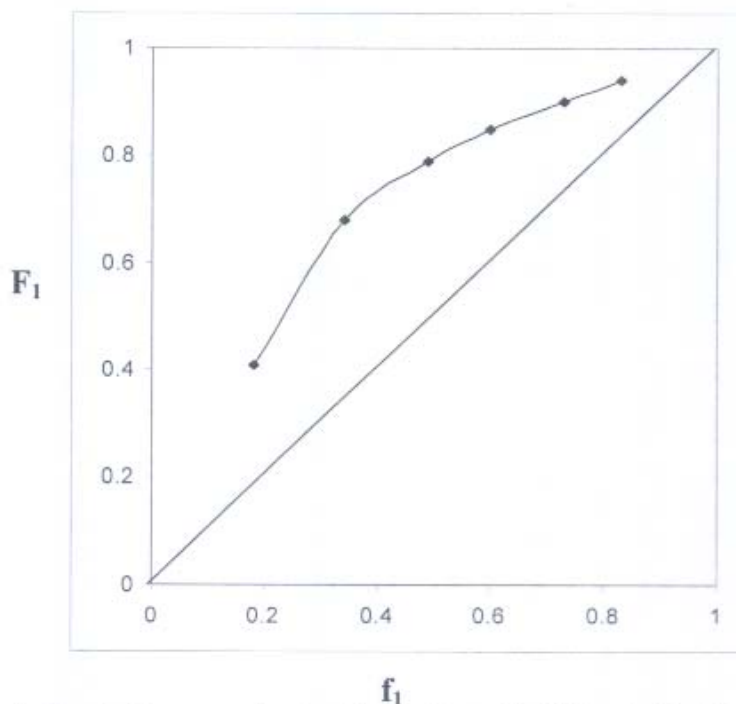


Fig (6) The relation between mole fraction of acrylonitrile in feed (f_1) and in copolymer (F_1).

Finally, we can conclude that the two methods for reactivity ratio measurement used in the present work

are good methods for prediction of copolymer composition and reactivity ratios.

References :

- 1- Baharmi, S. K; S. Bajaj, S.H. in High performance Acrylic Fibers, in J.M. S. Review of Macromolecular chemistry and physics Marcel Dekker Inc.; New York, 1996, **36**, 1-7 .
- 2- Herman F.M ; Norman G.G, "Encyclopedia of polymer Science and Technology", vol. 6, John Wiley and Sons Inc., New York, (1967).
- 3- Herman F.M, Norman G.G, "Encyclopedia of Polymer Science and Technology", vol. 1, John Wiley and Sons Inc., New York, (1985).
- 4- Herman F.M, Norman G.G, "Encyclopedia of polymer Science and Technology", vol. 4, John Wiley and Sons Inc., New York, (1960).
- 5- Ajaib S. B., Rajeev K., *Eur. Polym J.*, 2001, **37**, 1827 .
- 6- Nursel P., Nureltin S., Olgan G., Zakir M. O. Rzaev, *Eur. Polym. J.*, 2001, **37**, 2443 .
- 7- Gan L.H., Roshan G.D., Gan Y.Y., *Eur. Polym. J.*, 1998, **34**, 33 .
- 8- Brandrup J., Immergut E.H., and Grulke E.A., "Polymer Handbook" wiley interscience, New York 1999.