

Effects of Number of Wells and Cavity Length in Limitation the Optimum Symmetric Multiple Quantum Well Laser

Maysam Tariq Al-Obaidi

**Department of Physics / Collage of Sciences
Al-Mostansiria University**

Abstract

In this research several main parameters/factors that effect on each of structures of semi-conductor lasers have been investigated. This investigation depends mainly on two procedures : (1) A classification for these parameters including each of threshold current density, injecting threshold carrier density, absolute threshold current density and their relations with each of number of wells and cavity length.(2) A simulation process for the previous parameters with variable values of number of wells and cavity length. Non ideal contribution to the total output current like Auger recombination, Interface recombination and Leakage recombination have also been estimated through the simulation process. In other words, this research is devoted to specify the optimum performance of multi-quantum well structure of semi-conductor laser.

The calculations were performed for a representative separate confinement (MQW) laser structure in GaAs/AlGaAs system of: 7.5nm as a QW size, 250 nm as a thickness of the waveguide region and 8nm as a barrier size.

I. Introduction

Single Quantum Well (SQW) and Multiple Quantum Well (MQW) laser structures, are promising candidates for use in high speed integrated optics and optical communications field because of their significant superiority in performance over conventional double hetero-structures (DH) [1]. Quantum Well (QW) lasers posses [1, 2]: (1) the high potential of lower threshold current density with lower temperature sensitivity. (2) Higher differential quantum efficiency. (3) Improved coherency with reduced lasing line-width (i.e., small line-width enhancement factor because of the specific refractive index inside (QW) structure). (4) Superior mode stability. (5) Larger modulation band-width and reduced chirping during modulation process. As a matter of fact, the

efficiency of (QW) laser structures can be improved by introducing a number of parameters that can determine the optimum design of this type of laser structures and the most important of these parameters are the number of the quantum well (v_{QW}) and the cavity length (L), which can be affected by the values of threshold current density and carrier injection levels as will be discussed in this research [3].

II. Theory and Analysis

The parameters that effect on number of wells and cavity length values in symmetric multiple quantum well (MQW) lasers are ; threshold current density (J_{th}), injecting threshold carrier density (N_{th}) and absolute threshold current density (I_{th}). It should be mentioned that our numerical calculations were performed for a representative separate confinement MQW laser structure in (GaAs/AlGaAs) system with specific waveguide parameters as shown in Fig. (1) [4].

The total threshold current density can be obtained by adding all current contributions as shown in Eq. (1) [5,6]:

$$J_{th} = J_{r,th} + J_{S,th} + J_{A,th} + J_{lk,th} \quad \dots\dots\dots (1)$$

Where:

$J_{r,th}$: is the radiative threshold current density.

: is the interface threshold current density.

$J_{A,th}$: is Auger threshold current density.

: is leakage threshold current density.

The effects of parameters (J_{th} , N_{th} & I_{th}) will be classified according to three classifications as will be discussed below.

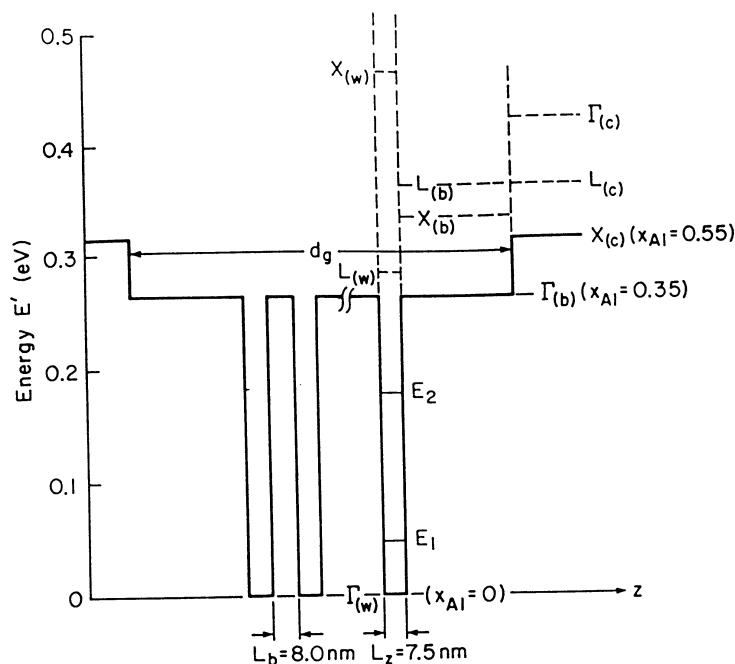


Figure (1) Representative Structure of GaAs/ALGaAs of MQW Laser.

A. The relationship between threshold current density (J_{th}), threshold carrier density (N_{th}) & number of the QW (v_{QW}):

The radiative QW component of the current in MQW laser is calculated from the integral over the spontaneous emission spectrum of the QWs [5]:

$$J_{r,th} = v_{QW} L_Z e \int_{E_{g,lb}}^{E_{g,b}} R_{SP}(E) dE \quad \dots\dots\dots (2)$$

L_Z is the size of well and the integration is taken over the transitions involving QW states only, with the lower cutoff at the effective band-gap ($E_{g,lb}$) of the QW and the upper cutoff at the band-gap ($E_{g,b}$) of the barrier. While R_{SP} represents the spontaneous emission and it can be calculated from the following equation:

$$R_{SP}(E) = r_0(E) |M_b|^2 \sum \rho_{r,jn}(E) [f_c (1 - f_v)_{E,jn}] \quad \dots\dots\dots (3)$$

Where:

r_0 : is the spontaneous emission prefactor.

M_b : is the transition matrix element.

$\rho_{r,jn}$: is the density of the energy states.

The spontaneous emission prefactor (r_0) is given by:

$$r_0(E) = e^2 n_g E / \pi m_0^2 \hbar^2 c^3 \epsilon_0 \quad \dots\dots\dots (3^-)$$

Here, (n_g) is the group index of the Q W material. It should be noted that the form of $R_{SP}(E)$ is largely determined by the density of states function ($\rho_{r,jn}$) and Fermi-Dirac function (f_v, f_c).

The interface recombination threshold current density ($J_{S,th}$) and by assuming identical interfaces in all of the structure, it could be simply given by [6] :

$$J_{S,th} = 2v_{QW} e N_{th} V_S \quad \dots\dots\dots (4)$$

V_S is the interface recombination velocity while the Auger threshold current density ($J_{A,th}$) is given by [6,7]:

$$J_{A,th} = v_{QW} L_Z e C_A N_{th} \quad \dots\dots\dots (5)$$

C_A is Auger coefficient but the Leakage recombination threshold current density ($J_{lk,th}$) is given by [7]:

$$J_{lk,th} = 2d_g N_b / \tau_b \quad \dots\dots\dots (6)$$

N_b is leakage carrier concentration at the barrier material and τ_b is the life-time of the electron in the barrier. Leakage carrier concentration (N_b) can be given by:

$$N_b = N_{c,b} \exp[(f_c - \Delta E_c) / K_B T] \dots\dots\dots (7)$$

$N_{c,b}$ is the regular effective density of states in (Γ) conduction band of the barrier, i.e.($N_{c,b} = [m_{c,b} K_B T / 2\pi\hbar^2]^{3/2}$),where $m_{c,b}$ is the effective mass of the electron in the barrier [6,7].

B. The relationship between threshold current density (J_{th}), threshold carrier density (N_{th}) and cavity length (L):

The threshold gain (g_{th}) is obtained from the local mode losses via the balance equation [8]:

$$G_{th} = \Gamma g_{th} = [\alpha_i + \ln(1/R) / L] \dots\dots\dots (8)$$

Here, (G) is expressed in terms of the local gain coefficient (g) and gain confinement factor (Γ). The mode loss is modeled by a combination of mirror loss α_m (i.e. $\alpha_m = \ln(1/R) / L$), intrinsic loss (α_i), and R is the reflectivity parameter that is defined by the two mirrors reflectivity R_1 & R_2 ($R = \sqrt{R_1 R_2}$). By substitution, the value of the threshold mode gain can be given by [8]:

$$G_{th} = \alpha_i + \alpha_m \dots\dots\dots (9)$$

A good approximation for a separate confinement MQW laser, is a linear relationship between Γ and v_{QW} , which for our representative structure of Fig(1) is with $L_z = 7.5\text{nm}$. and $d_g = 250\text{nm}$. and reads [4]:

$$\Gamma = 0.023 v_{QW} \dots\dots\dots (10)$$

Therefore, the relationship between (J_{th}), (N_{th}) and cavity length (L) can be obtained by using Eqs. (1),(8),(9) and (10).

C. The effects of absolute threshold current (I_{th}) on optimum number of wells (v_{QW}) and cavity length (L):

Besides injected carrier density N_{th} and threshold current density J_{th} , absolute threshold current density I_{th} is also an important operational parameter of semiconductor laser. For convenience, I_{th} has been normalized to $1\mu\text{m}$ of cavity width, which tends to decrease slightly toward smaller L (larger v_{QW}). These minima are largely determined by the reflectivity parameter (R) through the relation [9]:

$$I_{th}^{\min} = I_0 G_{th} L = I_0 [\ln(1/R) + \alpha_i L] \dots\dots\dots (11)$$

The quantity I_0 is essentially a function of the QW dimensions only, $I_0 = J_0 / G_0$, with $G_0 = g_0 \Gamma / v_{QW}$ where J_0 and g_0 are saturation parameters [9].

Therefore, the optimum number of QW can be obtained from:

$$(v_{QW})^{\text{opt}} = \text{Int} (G_{th} / G_0) \dots\dots\dots (12)$$

And the optimum cavity length at the minima I_{th} can be obtained from [9]:

$$L^{(opt)} \approx \ln(1/R) / (v_{QW} G_0) \dots\dots\dots (13)$$

III. Results and Discussions

By using Eqs. (1),(8), (9) and (10) and table (1)and (2) and as show in Figs.(2) and (3), the maximum number of QWs that can be accommodated with the chosen waveguide parameters is 16. One observes the expected general trend of increasing N_{th} with decreasing L and/or v_{QW} . as a consequence of the QW gain saturation. The series of J_{th} curves for constant L exhibit minimum near $N_{th} \approx 3.5 \times 10^{18} \text{ cm}^{-3}$. Below N_{th} about $2.5 \times 10^{18} \text{ cm}^{-3}$, J_{th} starts to increase rapidly approaching a vertical asymptote that corresponds to the transparency carrier density of $N_{tr} \approx 1.8 \times 10^{18} \text{ cm}^{-3}$. Also it should be mentioned that the interface recombination would become relatively more severe at these lower N_{th} values. So to keep N_{th} below about $3 \times 10^{18} \text{ cm}^{-3}$ (as a candidate operation range), one needs at least 16 QWs for $L=30 \mu\text{m}$, 8 QWs for $L = 60 \mu\text{m}$, 4 QWs for $L =125\mu\text{m}$, and 2 QWs for $L=250 \mu\text{m}$. For longer cavities the J_{th} minimum disappears. Obviously, less is to be gained by increasing v_{QW} when the laser cavity is longer.

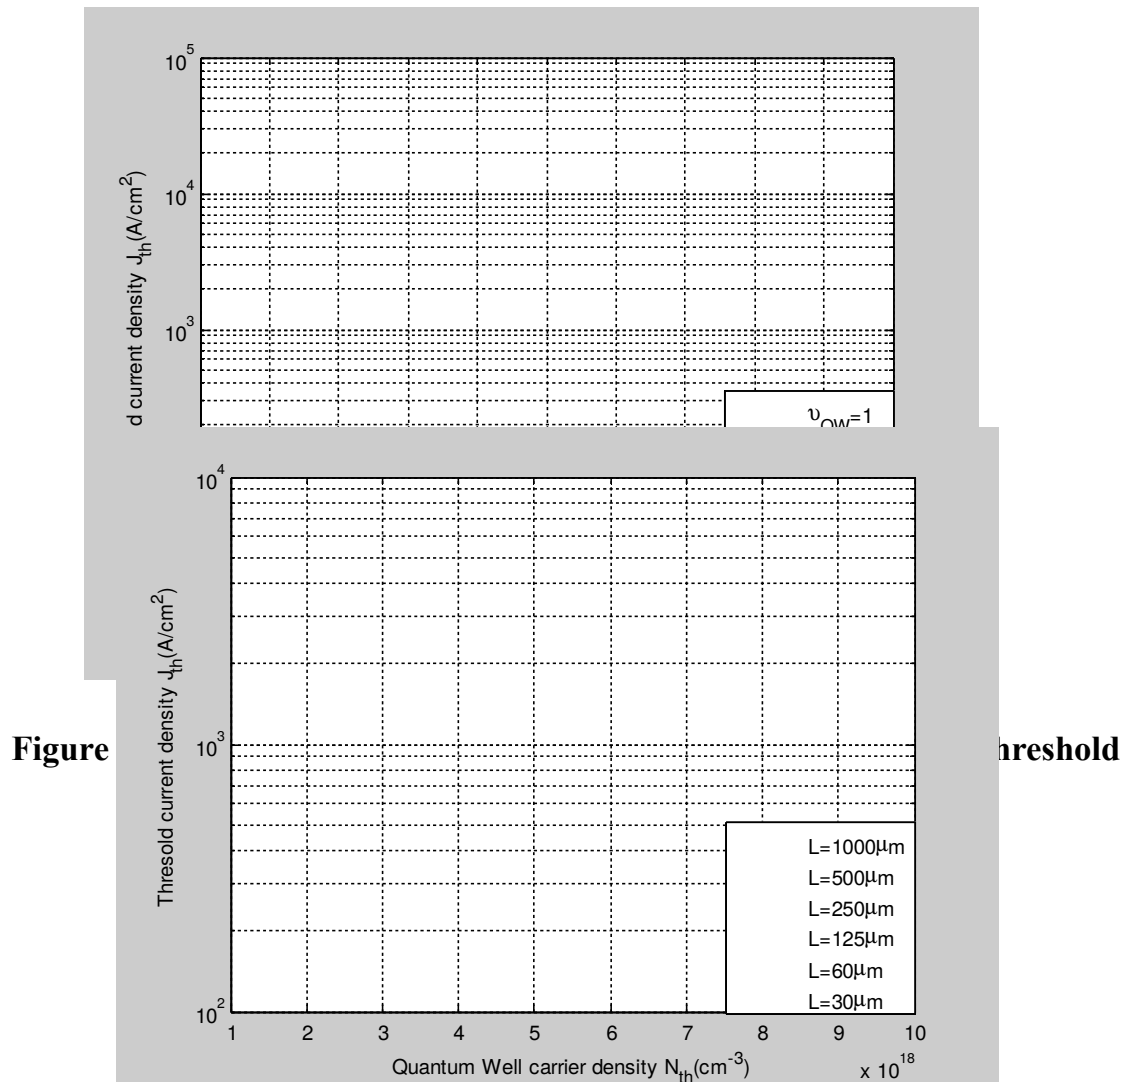


Figure (3) Relationship Between Threshold Current Density and Threshold Carrier Density with Value of Cavity Length.

Table (1)[4]

Densities of States and Fermi-Dirac Probability Function for Conduction and Valence Bands and N_c and N_v Expressions

Parameter	Expression
Fermi-Dirac probability function for conduction band	$f_c(E_c) = \frac{n}{N_c} e^{\left(\frac{-E_c}{KT}\right)}$
Fermi-Dirac probability function for valence band	$f_v(E_v) = \frac{P}{N_v} e^{\left(\frac{-E_v}{KT}\right)}$
Density of State for conduction band	$\rho_c(E) = 4\pi \left(\frac{2m_c}{h^2}\right)^{3/2} E^{1/2}$
Density of State for valence band (ρ_{vj})	$P = \sum_{i=l,h} \int \frac{\rho_{vj}(E) dE}{1 + e^{\frac{E-E_v}{KT}}}$
N_c	$2 \left(\frac{2\pi m_c KT}{h^2}\right)^{3/2}$
N_v	$2 \left(\frac{2\pi KT}{h^2}\right)^{3/2} (m_{lh}^{3/2} + m_{hh}^{3/2})$

The alternate representation of I_{th} with cavity length L as a variable parameter is presented in Fig.(4) ,which was chosen for demonstrating the influence of interface recombination, Auger recombination, and carrier leakage respectively.

In this figure, a SQW, 3-QW_s, and 6-QW_s laser are compared with each other , which was determined in order to analyze the influence of these nonradiative and leakage mechanisms.

Fig.(4) shows a striking increase of I_{th} towards short cavity length, which is a direct consequence of the gain saturation in the QWs at high injection levels. With increasing QW number, the shifts will increase towards smaller L values. The position of the anomalous increasing might be affected by Auger recombination, leakage carrier, but only marginally by interface recombination.

Table(2)[4]

Some Parameters Values of GaAs/AlGaAs Multiquantum Well Laser

Parameter	Symbol	Value
Operating wave length	Λ	1.3 μ m
Group velocity	c/μ_g	$3 \times 10^8/5$
Group refractive index	μ_g	5
Interface recombination group velocity	v_s	100cm/s
Effective mass of electron /Rest mass of electron	$\frac{m_C}{m_0}$	0.35
Effective mass of electron /Rest mass of electron	$\frac{m_{C,b}}{m_0}$	0.11
lifetime in the barrier	τ_b	1ns
Waveguide region of thickness	d_g	250nm
Linear current density saturation parameter	J_0	220A/cm ²
Linear gain saturation parameter	g_0	1250cm ⁻¹
Intrinsic loss	α_i	5cm ⁻¹
Reflectivity	R	0.3
Auger coefficient	C_A	5×10^{-30} cm ⁶ /s
Matrix element/Rest mass of electron	$\frac{ M_b ^2}{m_0}$	19.7+5.6y x=0.47y for

		$\text{In}_{1-x}\text{Ga}_x\text{As}_y\text{P}_{1-y}$
Effective mass of heavy hole/Rest mass of electron	$\frac{m_{hh}}{m_0}$	$0.62+0.05x$
Effective mass of light hole/Rest mass of electron	$\frac{m_{lh}}{m_0}$	$0.11+0.03x$
energy gap of light hole band	$E_{g,hl}$	0.94eV
energy gap of barrier	$E_{g,b}$	1.2eV
Band offset	$\Delta E_c(\text{eV})=0.34(1-x)+0.371x$	
Quantum well size	L_z	7.5nm

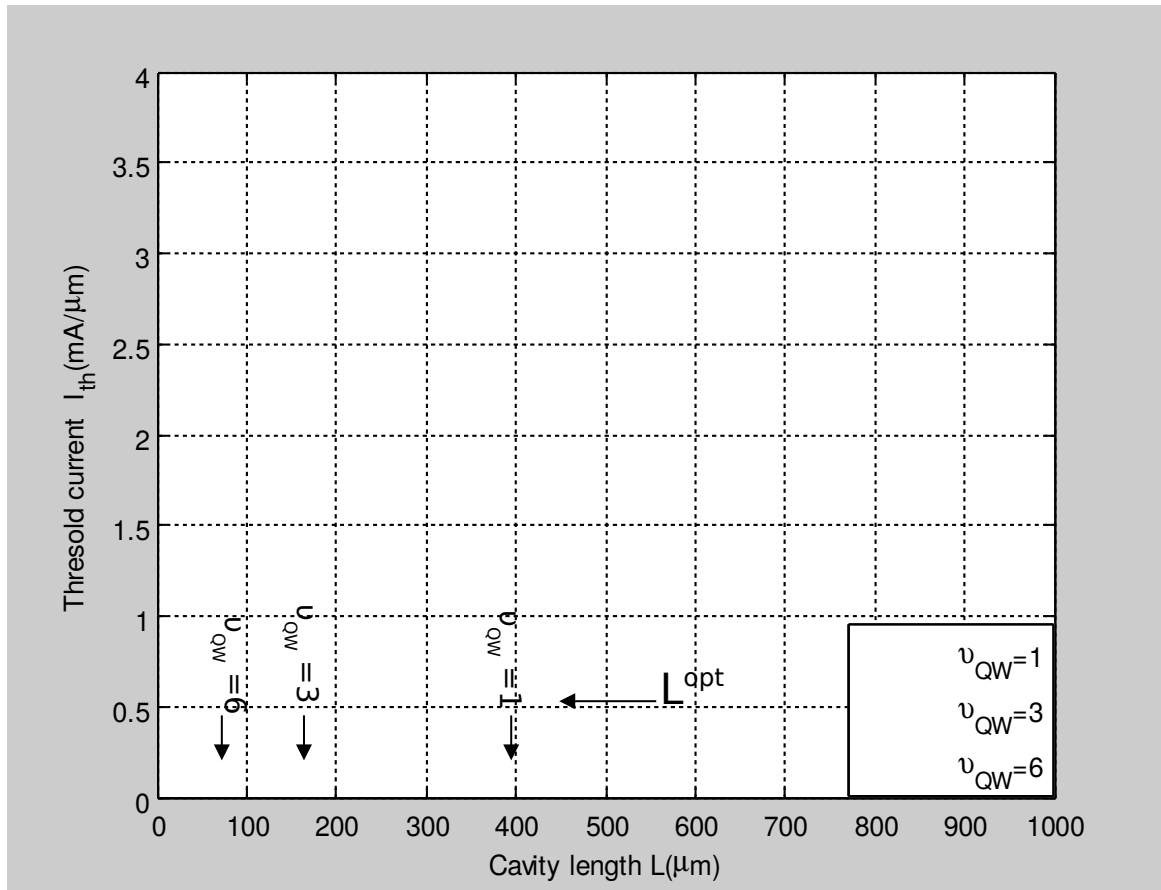


Figure (4) Relationship between Threshold Current and Cavity Length with v_{QW} . Different Values of Number of Wells.

Conclusions

From the previous results, it can be concluded that our representative system of GaAs/AlGaAs has a dominant effect at longer cavity lengths, including the

flat threshold current minimum, where the contributions of the non-ideal non-radiative transitions become small.

The system has determined the maximum number of the QW_s that can be accommodated with the chosen waveguide parameters to be 16, and the maximum cavity length to be in the range of (250μm). Higher cavity length values might cause J_{th} disappearing.

The intermediate range of N_{th} between (2.5-3) 10¹⁸ /cm³, can be considered as optimal for all practical purposes. So for operation in this favorable injection regime of N_{th}, one can choose either long cavities or large number of wells (QW_s) in order to avoid carrier losses, which demonstrates the preference of MQW over SQW laser structure.

In Fig.(4), there is an anomalous increasing of I_{th} with increasing v_{QW} and towards short cavity length L. This anomalous region has been estimated to be caused essentially by Auger recombination and carrier leakage. Finally, and as shown in Fig.(4), the optimum cavity length at minimum I_{th} can be specified.

References

- [1] D. Wilt and A. Yariv, "A self-consistent static model of the double-heterostructure laser," IEEE Journal of Quantum Electronics, vol, QE-17, pp. 1941-1951, 1999.
- [2] N. Tansu, J.-Y. Yeh, and L. J. Mawst, "Extremely low threshold-current-density InGaAs quantum-well lasers with emission wavelength of 1215-1233 nm", Appl. Phys. Lett., vol. 82, no. 23, pp. 4038-4040, 2003.
- [3] S. Shirakata, M. Kondow, and T. Kitatani, "Temperature-dependent photoluminescence of high-quality GaInNAs single quantum wells", Appl. Phys. Lett., vol. 80, no. 12, pp. 2087-2089, 2002.
- [4] A. Partovi, A. M. Glass, T. H. Chiu, T. H. Liu, "High-speed joint-transform optical image correlator using GaAs/AlGaAs semi-insulating multiple quantum wells and diode lasers," *Optics Letters*, 18(11), pp. 906-908, 2000.
- [5] V.K. Kononenko, I.S. Manak, and S.V.Nalivko, "characteristics of symmetric multiple- quantum well heterostructures with broad-band controllable radiation" ,Proc. VIII Int. Symp. Advanced Display Technologies, pp.239-244 2005.
- [6] M. Dovrat, Y. Goshen, J. Jedrzejewski, I. Balberg, and A. Sa'ar, "Radiative versus nonradiative decay processes in silicon nanocrystals probed by time-resolved photoluminescence spectroscopy," *Physical Review B*, vol. 69, 155311, Apr 2004
- [7] M.J.Hamp,D.T.Cassidy,B.J.Robinson,Q.C.Zhao,D.A.Thompson,and M.Davies, " Effect of barrier height on the uneven carrier distribution in

symmetric multiple- quantum well lasers”, IEEE Photon. Technol. Lett. 10,1380 -1382 (2006).

- [8] B. R. Nag, “ Boundary conditions for the heterostructures multiple- quantum well lasers”, J. Appl. Phys., vol. 70, no. 8, pp. 4623-4625, 2003.
- [9] F. Qiao, C. Zhang, J. Wan, and J. Zi, “. Photonic Multiple quantum-well laser.” *Appl. Phys. Lett.*, vol.77, no. 23, pp. 1208-1211, 2009.

ملخص البحث

تم في هذا البحث دراسة عدد من العوامل المؤثرة في كل من عدد الابر الكمومية (Quantum Wells) و طول البئر الواحد (cavity length) في تركيب نبائط ليزرات اشباه الموصلات و تعتمد هذه الدراسة بشكل اساسي على عمليتين اساسيتين :

- 1) عملية تصنيف لهذه العوامل متضمنة كلا من: كثافة تيار العتبة (threshold current density), كثافة حاملات الحقن (injection threshold current density) و كثافة التيار المطلق (absolute threshold current density).
 - 2) عملية محاكاة (simulation proses) لكل من العوامل السابقة بوجود قيم متغيره لكل من عدد الابر و حجم البئر الواحد.
- كما تمت خلال البحث دراسة العديد من الاسهامات غير المثالية (الانتقالات غير المشعة) و التي تؤثر على القيمة الكلية للتيار الخارج (total output current) مثل:
- الاتحاد الناتج عن ظاهرة اوكير (Auger recombination)
 - الاتحاد عند السطح (Interface recombination)
 - اتحاد تيار التسرب (leakage recombination)
- ان هذا البحث يهدف بشكل اساسي الى تحديد افضل تركيبه لنبائط ليزرات اشباه الموصلات ذات التركيب المتعدد الطبقات و المتماثل (symetric multiple quantum well laser structure) ان الحسابات المعتمده في هذا البحث كانت مخصصه لنبيطه مؤلفه من مادة ال (GaAs/AlGaAs) ذات طول بئر يصل الى (7.5nm) و سمك لمنطقة متجه الموجه يصل الى (250nm), و حجم حاجز يصل الى (8nm).