



وزارة التعليم العالي والبحث العلمي
جامعة ميسان
كلية التربية الاساسية

مجلة ميسان للدراسات الاكاديمية العلوم الانسانية والاجتماعية والتطبيقية

ISSN (Paper)- 1994-697X

(Online)- 2706-722X



المجلد (23) العدد (50) حزيران (2024)

مجلة ميسان للدراستات الاكاديمية

العلوم الانسانية والاجتماعية والتطبيقية

كلية التربية الاساسية - جامعة ميسان - العراق

ISSN (Paper)- 1994-697X

(Online)- 2706-722X

المجلد (23) العدد (50) حزيران (2024)

ISSN
INTERNATIONAL
STANDARD
SERIAL
NUMBER
INTERNATIONAL CENTRE

OJS / PKP
www.misan-jas.com

IRAQI
Academic Scientific Journals



ORCID

OPEN ACCESS



journal.m.academy@uomisan.edu.iq

رقم الايداع في دار الكتب والوثائق بغداد 1326 في 2009

الصفحة	فهرس البحوث	ت
14 - 1	Detection of Exoenzyme Effectors and Determination The MIC of Antibiotics for Pseudomonas Aeruginosa Isolated from Ear Infections Patients in Basrah Province, Iraq Ayad Abdulhadi Waham Lina A. Naser	1
25 - 15	Effect of Addition Zirconia/Chitosan Filler on Mechanical Properties of Heat Cure Polymethyl Methacrylate Resin Shahad Lateef Mohammed Firas Abdulameer Farhan	2
33 - 26	A Case :The Politicization of Love in American Poet Laureates Inaugural Poems Study of Amanda Gorman and Maya Angelou Hussein Mezher Jasim	3
46 - 34	Analytical Study in Gynecology: Designing Treatments for Polycystic Ovary Syndrome Otoor Hassoon Abdulameer Raghad S. Shamsah	4
60 - 47	African Development in the New Millennium: Going Beyond the "Good Governance" Debate Oluseyi Elijah AKINBODE Bimbo Ogunbanjo	5
91 - 61	Environmental Foreign Policy and Diplomacy in an Unequal World Bimbo OGUNBANJO	6
101 - 92	Dysfunctional American Family and Spiritual Decay in Edward Albee's Me, Myself and I Habeeb Lateef Kadhim AL-Qassab	7
113 - 102	The relationship of salivary cortisol and Volatile Sulfur Compounds with Halitosis among pregnant woman Mareim Radhi Abd Al Nabby Abbas Almizraqchi	8
125 - 114	Microbiota Revelations: First-time Prevotella spp. Identification in Iraq Pediatric Autism Aladien Aurebi Muhawi Yasin Yacoup Yousif. Al-Luaibi	9
142 - 126	Effect of Electronic Cigarette on Oral Health Haneen A. alyaseen Zainab A. Aldhafer	10
157 - 143	A Narrative Stylistic Analysis of (Voice) in Doris Lessing's "An Old Woman and her Cat" in Terms of Gerard Genette's Model Narjis Abdul-Kareem Majeed Hameed Jassim	11
167 - 158	The Role of Erythritol/Glycine Air Polishing Powder In Non-Surgical Periodontal Mohammed Khalid Ayoob Hayder Raad Abdulbaqi	12
176 - 168	cytological and cytomorphological comparative study of oral mucosa in diabetes mellitus and nondiabetics in Misan Governorate. Noor Saeed Aneed Ali Khalaf Ali Maitham Abdel Kazem Daragh	13
194 - 177	اشكالية الانتواء لدى يهود امريكا رواية "حتى الازمة" للكاتب شمعون هالكين ((نموذجاً)) عمار محمد خطاب	14
208 - 195	قياس تركيز ^{226}Ra و ^{222}Rn في مجموعة من عينات المخلفات النفطية (Oil sludge) من بعض حقول نفط ميسان باستخدام كواشف الاثر النووي (CR-39) مرتضى محمد عطية	15
221 - 209	دور الشفافية في مكافحة الفساد الإداري في تعزيز حقوق المواطن العراقي محسن قدير محمد نور الدين ماجدي	16


231 - 222	الأثار التربوية للمعاد أياد نعيم مجيد	17
244 - 232	الأنزياحات الرمزية في شعر ماجد الحسن نائل عبد الحسين عبد السيد	18
266 - 245	التحرش الجنسي وحكمه الفقهي (دراسة نقدية للمواد القانونية ذات العلاقة في القانون العراقي) فلاح عبد الحسن هاشم	19
283 - 267	الشمول التشريعي بين النفي والإثبات أياد عبد الحسين مهدي المنصوري	20
299 - 284	دور البرامج الحوارية في فضائيات الأحزاب الإسلامية بترتيب أولويات الجمهور العراقي ازاء القضايا الوطنية حسين امير عباس عادل عبد الرزاق مصطفى	21
312 - 300	العلاقات الدلالية في تفسير معارج التفكير ودقائق التدبر لعبد الرحمن الميداني (1425هـ) مصطفى صباح مهوود انجيرس طعمة يوسف	22
326 - 313	دور النمذجة في أدراك المتعلمين البصري لأساسيات المنظور في مادة التربية الفني حسين رشك خضير	23
346 - 327	فاعلية استراتيجية الرؤوس المرقمة في تحسين الدافعية لدى تلاميذ الصف الخامس الابتدائي في مادة اللغة الإنكليزية منى عبد الحسين حصود فاطمة رحيم عبد الحسين	24
360 - 347	دور المدقق الخارجي في تقليل مخاطر العرض الالكتروني للتقارير المالية محسن هاشم كرم النوري	25
377 - 361	صفات المنهج التربوي في القرآن وآليات تحقيقه دراسة تحليلية تفسيرية أحمد نذير يحيى مزيداوي	26
393 - 378	طقوس الدفن في بلاد الأناضول وأسلوب فصل الجماجم في العصر الحجري الحديث سارة سعيد عبد الرضا فاضل كاظم حنون	27
407 - 394	معالم القصة القرآنية ومعطياتها حيدر كريم عودة	28
423 - 408	تأثير التفكير المنهجي المنظومي لمادة الأحياء لطلبة المرحلة الإعدادية استنادا الى استراتيجية PLAN رجاء جاسم هاتف	29
442 - 424	الفضاءات المترية الجزئية ومفهوم النقطة الثابتة بشرى حسين سيد	30
451 - 443	المقاربة الطبيعية للغة على عبد الكاظم حميد ضمير لفته حسين	31



ISSN (Paper) 1994-697X

ISSN (Online) 2706-722X

DOI:

<https://doi.org/10.5463/3/2333-023-050-002>

Effect of Addition Zirconia/Chitosan Filler on Mechanical Properties of Heat Cure Polymethyl Methacrylate Resin

Shahad Lateef Mohammed¹, Firas Abdulameer Farhan²

Department of Prosthodontics, College of Dentistry, University of Baghdad, Baghdad, Iraq

¹E-mail: shahadlateef024@gmail.com<https://orcid.org/0009-0000-6921-2261>²firas.farhan@codental.uobaghdad.edu.iq

ABSTRACT:

The preferred material for creating removable prosthesis is acrylic resin. for the reintegration of edentulous patients due to its good aesthetics, precise fit, low cost of equipment, and ease of clinical and laboratory manipulation. Acrylic resin exhibited relatively unsatisfactory characteristics like low impact and transverse strength. However, the acrylic resin was reinforced by adding filler materials like glass fibers or mixing two powders like zirconia and chitosan. The goal of this investigation was to explore how adding nanoscale zirconia with micrometer size of chitosan (zr-ch) filler with two percentages of 1% wt. and 5% wt. and two ratios of zr-ch (2:1 and 1:2) according to a pilot study and evaluate the surface hardness, impact and transverse strength. Ninety heat-cure acrylic samples were divided into three groups (each group 30 samples) based on the percentage weight of filler added to the acrylic mixture and the ratio between the nanoparticles of zirconia with a micrometer of chitosan particles. For control group (c) without addition, group A1 with 1% wt. and a ratio of 2:1 (zr-ch) and group A2 with 5% wt. and a ratio of 1:2. Each group was tested with impact strength, transverse strength and surface hardness (10 samples for each test). The zr-ch mixture ratio was prepared and selected according to the pilot study. A sharp testing device was used to measure the impact strength while a hardness shore D device measured surface hardness and the final test was transverse strength which was tested by a universal Instron machine. The data were statistically analyzed by IBM SPSS statistics (version 24). The findings of the present study showed significant differences in surface hardness and transverse strength throughout the various study groups. However, the group A2 variation in impact strength was discovered to be nonsignificant, while the group A1 difference was shown to be significant. The best result for all three tests was obtained in the group A1. The adding zr-ch mixture improved surface hardness, impact and transverse strength, which improved acrylic denture base.

Keywords: acrylic resin; zirconia-chitosan filler; transverse strength; surface hardness and impact strength.

INTRODUCTION:

Acrylic denture base resin is frequently used to make removable prosthetics. This substance is imperfect, its use and appeal come from a blend of qualities rather than just a desired one. Even though it satisfies cosmetic standards it falls far short of meeting prosthetic other requirements. Acrylic resin is weak as a base material for dentures because of its susceptibility to impact failure externally brought on by dropping of the dentures and failure due to fatigue inside the mouth brought on by biting force of the occlusal surfaces (Alla, R. K., 2013). There have been numerous attempts to reinforce acrylic denture base resin, such as the insertion of metallic wire; however, the primary problem with using metallic wire is that it fails to bond well to the matrix of acrylic resin. (Vojdani M. and Khaledi A., 2006). The impact strength has been improved by adding a rubber phase to the bead polymer, however the cost has gone up (Jagger D.C. et al., 1999).

Nanotechnology has recently entered the prosthetics industry for medical and material advancement goals. Academics and researchers from all around the world are interested in metal oxides because of their large range of potential applications in industries including materials science, medicine, and industrial inspection (Hussein NA and Ali NA., 2022). By adding nanoparticles, resin materials can be combined with metallic substances, fibres, and oxides to create nanocomposites with better biomechanical properties. (Al-Sammraie, M. F., Fatalla, A. A., 2024). The study's use of nano-zirconia as a filler was motivated by its ability to enhance the mechanical characteristics of acrylic resins. Zirconia has several advantageous qualities, including superior mechanical strength and toughness, resistance to abrasion and biocompatibility (Ayad N.M. et al., 2008). Researchers found that nano ZrO₂ boosted the antifungal activity of 3D-printed denture base polymer (Fareed Al-Sammraie, M., A Fatalla, A., 2023). Another research enhanced impact and transverse strength of repaired acrylic resin with incorporation of ZrO₂ and Al₂O₃ (Al-Judy H. J., 2016). Growing interest has been shown in modifying and using chitosan in the biomedical sectors because of its biocompatibility, biodegradability, nontoxic qualities, and antibacterial activity (Kong, M. et al., 2010). Chitosan also was used to enhance the properties of titanium for implant applications, PCL/Chitosan/cinnamon watery extract composite were deposited on commercially pure titanium specimens using electro spinning technique (Khadija Sahib et al., 2023). The present investigation looked at the impact of incorporating nanoscale zirconia-chitosan (zr-ch) filler with two percentages of 1% wt. and 5% wt. and two ratios of zr-ch (2:1 and 1:2) according to a pilot study and evaluate the impact strength, transverse strength, and surface hardness.

Materials and methods:

Preparation of zirconia and chitosan mixture:

Based on the findings of a pilot investigation to determine optimal concentration of nano-zirconia-chitosan powders (zr-ch) to use as a filler material for heat-cured acrylic resin to improve mechanical properties. The selected percentages were 1% wt. with a ratio of 2:1 (zr-ch) and 5% wt. with a ratio of 1:2 as group A2. A field emission scanning electron microscope (FESEM) was used to confirm the particle size and distribution of the zr-ch mixture. The zr-ch powders were mixed for 10 minutes using a ball milling machine.

Samples preparation and grouping:

Ninety acrylic samples were divided into three groups (30 samples for each) according to the percentage and ratio of the zr-ch mixture that was added to the acrylic sample. For control group (c) without adding a zr-ch mixture, group A1 with 1% wt. and a ratio of 2:1 (zr-ch) and group A2 with 5% wt. and a ratio of 1:2. Each group was tested with impact strength, transverse strength and surface hardness (10 samples for each test). Different sample patterns were designed by three-dimensional software and fabricated from plastic plates using a laser-cutting machine according to each test Figure (1).

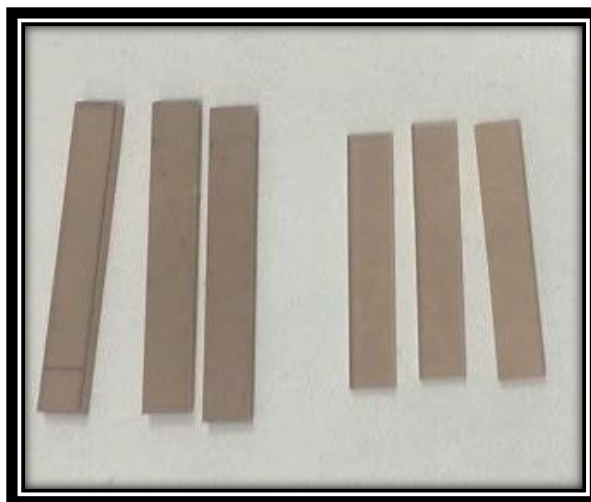


Figure (1): plastic sample patterns

Acrylic samples were produced by placing the plastic pattern in the lower half of the metal flask with dental stone as investment material and pouring the second layer after applying separating media to produce a sample mold to receive acrylic resin. The acrylic resin was mixed as directed by the manufacturer with the powder/monomer ratio 3:1 (22g to 10 ml). The zr-ch mixture was added to the acrylic mixture according to the mentioned groups, packed into the sample mould after reaching the dough stage and cured with a short cycle by water bath according to the manufacturer's instructions. The temperature was raised from ambient temperature to 70 °C in 30 minutes and left in water for another 30 minutes. Subsequently, the degree of temperature was gradually increased for 30 minutes to reach 100 °C and remained for 30 minutes.

Impact strength test:

The impact strength was conducted by the Charpy impact tester according to ISO 179, 2000. The sample dimensions were 80 mm x 10 mm x 4 mm.

Surface hardness and transverse strength tests:

The surface hardness was achieved using a shore D hardness durometer hardness tester (ANSI/ADA., 1999). The shore D hardness was recorded as the maximum value obtained by applying firm and rapid pressure to the indenter. Sample measurements for surface hardness and transverse strength testing were 2.5 mm × 10 mm × 65 mm.

A Universal Instron testing apparatus was used to perform the transverse strength evaluation, namely the micro-computer testing machine (JIANQIAO Testing Equipment) under the ANSI/ADA specification No. 12, 1999 as shown in Figure (2). The data was analyzed using descriptive statistics, multiple pairwise comparison tests, and the Tukey post hoc test. The software used in the study was SPSS version 24.

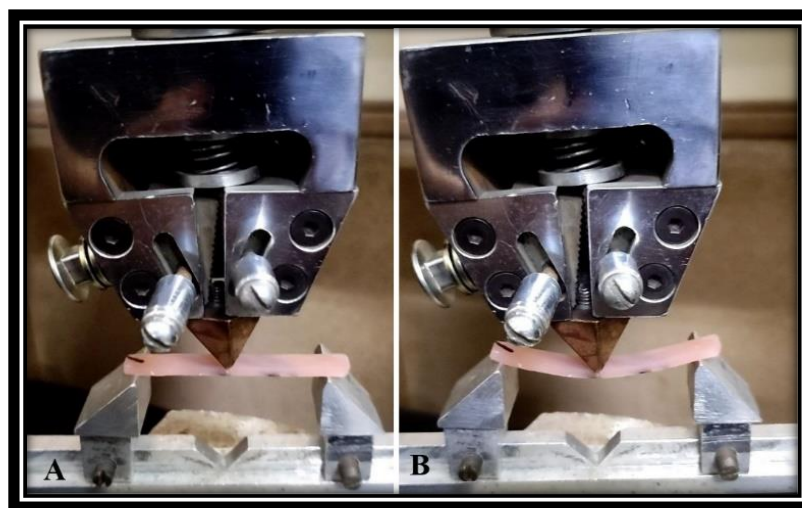


Figure (2): A- Sample before bending and B- Sample after bending before fracture

Results:

Field Emissions scanning electron microscope of filler particles and specimens:

FESEM images showed the particle size distribution. To confirm that zirconia is nanoparticles and chitosan is micro-particles as shown in Figure (3) and Figure (4).

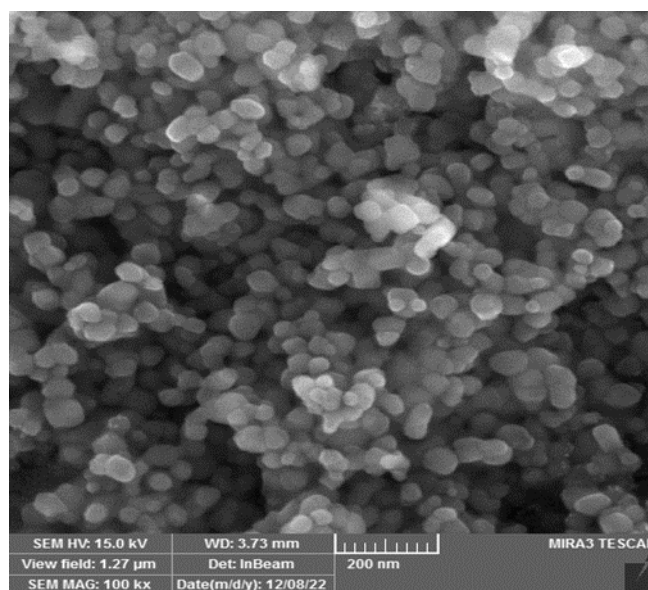


Figure (3): FESEM of nano zirconia powder

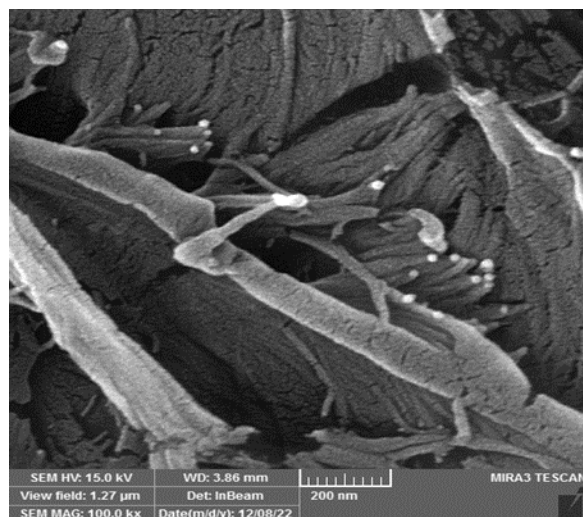


Figure (4): FESEM chitosan powder

FESEM analysis of tested samples displayed surface of group C Figure (5), groups A1 and A2 showed as shown in Figures (6), and (7). For A2 group there were filler agglomerations.

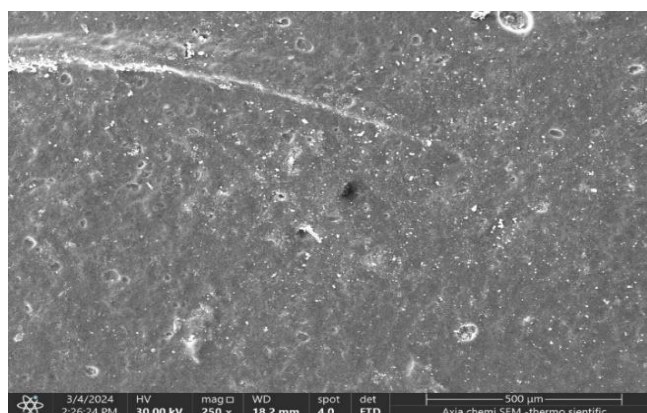


Figure (5): FESEM of the sample surface of group C

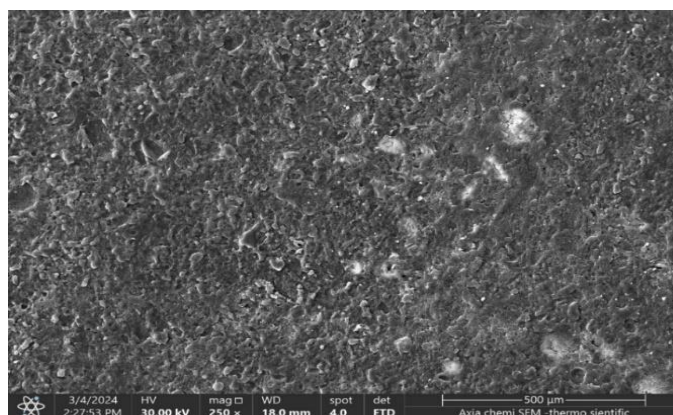


Figure (6): FESEM of the sample surface of group A1

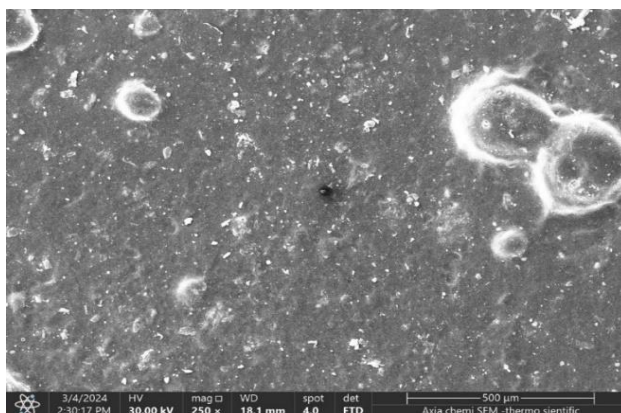


Figure (7): FESEM of the sample surface of group A2

Impact strength:

The impact strength mean value was increased in group A1 (12.788) more than in group A2 (11.155) and group C (10.574) as listed in Table (1). A non-significant variance with a P-value less than 0.05 was seen between group A2 and group C, while there was significant variation between the A1 and C groups. as shown in Table (2).

Table 1: An analysis of impact strength descriptive statistics

Groups	N	Mean	SD
C	10	10.574	0.676
A1	10	12.788	0.696
A2	10	11.155	0.492

Table 2: Tukey HSD multiple pairwise comparisons

Groups (I)	Groups (J)	Mean Difference (I-J)	P-value
C	A1	-2.214	0.000
	A2	-.581	0.115
A1	A2	1.633	0.000

Surface hardness:

Table (3) displays descriptive data for the surface hardness assessment, in which the highest mean value for the heat cure acrylic-test group (86.120) is shown in the A1 group and the lowest mean value (82.390) is shown in the C group, while for A2 group the mean value of surface hardness increased (85.090) in compare to C group but still lower than the mean value of A1 group. Table (4) shows a significant difference between the studied groups with a P-value less than 0.05.

Table 3: Descriptive Statistics of Surface hardness

Groups	N	Mean	SD
C	10	82.390	.922
A1	10	86.120	.869
A2	10	85.090	.631

Table 4: Pairwise comparisons between groups for surface hardness

Groups (I)	Groups (J)	Mean Difference (I-J)	P-value
Control	A1	-3.730	0.000
	A2	-2.700	0.000
A1	A2	1.030	0.023

Transverse strength:

Descriptive statistics show that transverse strength increased significantly in groups A1 (87.207) and A2 (85.177) compared to group C (81.175), with group A1 having the greatest value. The highest mean value was in group A1 and lowest in group C shown in Table (5). There were significant differences among groups with a P-value less than (0.05) as seen in Table (6) using multiple comparisons test.

Table 5: Transverse strength descriptive data

Groups	N	Mean	SD
C	10	81.175	0.797
A1	10	87.207	0.629
A2	10	85.177	0.815

Table 6: Pairwise Comparisons between groups for transverse strength

Groups (I)	Groups (J)	Mean Difference (I-J)	P-value
Control	A1	-6.031	0.000
	A2	-4.002	0.000
A1	A2	2.030	0.000

Discussion:

The objective of the present investigation was to analyse the acrylic denture base's mechanical characteristics after adding zr-ch filler in different percentages to the heat cure acrylic.

The use of zirconia and chitosan filler in the current study was motivated by the widespread practice of incorporating natural fillers into polymers to enhance their strength due to the environmentally friendly characteristics associated with such fillers. Researchers have made several experiments to improve the properties of denture base materials, some of these attempts were made by adding fibers as reinforcement to PMMA and forming a new composite with better properties (Abdulrazzaq Z.A., and Khalaf B. S., 2023). Since other studies (Ayad N.M. et al., 2008, Alhava A. et al., 2017, Al-Harbi FA. et al., 2019) did not use surface treatment with silane and showed promising results it is not required for the nano zirconia in this work to be silanated (Leão RDS et al., 2023).

In this research, the addition of zirconia-chitosan filler led to a rise in the mean value of impact strength, surface hardness and transverse strength in both experimental groups in contrast to the control group, but the most increase was obtained in A1 group. In the impact strength test, this increase was statistically significant For the A1 group, but for the A2 group, it was statistically non-significant.

Although both concertation enhanced impact strength, the best gain was observed in A1. The decrease at greater concentrations might be attributable to numerous variables, including the likelihood of filler agglomeration, the extent of the additive dispersion inside the PMMA, and the creation of an interfacial layer between the PMMA matrix and the additives (Abushowmi T.H., et al., 2020).

The chemical interaction between the basic PMMA and the nanoparticles may be lessened if the nanoparticles aggregate because of their vast surface area and elevated surface energy (Chladek G, et al., 2019). The rise in impact strength at smaller amounts may be due to the interface shear strength between chitosan and the polymer matrix, which encourages cross-linking or supramolecular bonding (Al-Harbi FA. et al., 2019, Choksi RH, et al., 2016). The decreasing compatibility of higher chitosan levels testing particles to resin matrix that led to failure owing to research particle slippage under increasing stress applications may be the cause of A2 fall in impact strength (Gad MM, et al., 2018, Protopapa P et al., 2011). Surface hardness values increased in this investigation, and this increase was statistically significant for both experimental groups. ZrO₂ has ionic bonding with oxygen ions together filling vacancies to produce appropriate material qualities which include high toughness and high hardness. Strong ionic interatomic bonding in nanoparticles produces the material's desired properties, such as hardness and strength. It implies that dispersing nanoparticles in a matrix would improve the matrix's strength and hardness (Ellakwa A., 2008). The chitosan effect on surface hardness could be explained by the impact of chitosan on the porosity of acrylic. A study found that the addition of chitosan with 1 and 2 % to acrylic denture base reduces the porosity (Ismiyati T, and Alhasyimi AA., 2022). Since the porosity is inversely proportional to surface hardness, therefore there was an increase in hardness after the addition of zirconia-chitosan filler. according to prior research, the incorporation of zirconia-polymerized acrylic into acrylic resulted in an increase in hardness (Rasan D and Farhan FA, 2023). Furthermore, a further investigation reported a significant increase in transverse strength due to the incorporation of ZrO₂-Al₂O₃ (MAH, B., and Aljafery, A. M., 2015). Surface hardness substantially rose, according to a different investigation after the incorporation of 3% silanated nano zirconia (Al-Hiloh S A, and

Ismail I J A., 2016). The transverse strength significantly increased as compared to the control group. For both experimental groups, this rise was statistically significant, however zirconia-chitosan filler at the A1 group provided the most benefit. This improve in transverse strength may be the result of transformation toughening, this is the mechanism by which zirconia absorbs the energy of fracture development and transitions from a tetragonal to a monoclinic phase.

Additionally, as ZrO crystals expand during this process, compressive stress is applied to the fracture, stopping its development (J. A. Kenneth, C., 2013). More filler particles after attaining matrix saturation cause disruption in the continuity of the resin matrix, and higher filler percentages led to more defects that affect material strength and particle clustering inside the resin (Nejatian T et al., 2020), Furthermore, the distribution of chitosan in the resin matrix is the reason for the improved strength. Chitosan interacts with denture base resin through reactive groups (-COOH, CH₁, etc.). The physical or mechanical bond that might form because of difference in size between the chitosan and the resin may increase strength. Additionally, at greater concentrations, the availability of functional groups to react with the monomer may be limited due to the distribution of the particles in space and the formation of multilayer coupling agents around the particles. The research of Karci et al, Maitra et al, and Sodagar et al reported decreases in transverse strength owing to uneven distribution, and insufficient retention of composite particles inside the resin matrix during the examination of different chitosan concentrations (Karci M, et al., 2019, Maitra U et al., 2009, Sodagar A, et al., 2013). A related study found that silica from Iraqi rice husk was effectively added to the high-impact heat-cured acrylic resin at a weight of 1%, greatly improving the mechanical characteristics of the high-impact heat-cured acrylic (Khairi AW, and Naji GA., 2023).

Conclusion:

The adding of (zr-ch) significantly improved surface hardness, transverse and impact strength, which improved the heat cure acrylic denture base.

References:

- Abushowmi, T. H., AlZaher, Z. A., Almaskin, D. F., Qaw, M. S., Abualsaud, R., Akhtar, S., Al-Thobity, A. M., Al-Harbi, F. A., Gad, M. M., & Baba, N. Z. (2020). Comparative Effect of Glass Fiber and Nano-Filler Addition on Denture Repair Strength. *Journal of prosthodontics : official journal of the American College of Prosthodontists*, 29(3), 261–268.
<https://doi.org/10.1111/jopr.13124>.
- Abdulrazzaq Z.A., Khalaf B. S. (2023). Natural Fibers Reinforcement of Denture base materials: Natural Wool Reinforcement (A Review of Literature). *Misan journal of academic studies*.
<https://doi.org/10.54633/2333-022-047-02>.
- Alla, R. K. (2013). "Dental materials science". New Delhi, Jaypee Brothers Medical Publishers (P) Ltd: 252 - 3.
- American Dental Association Specification No. 12 (1999). For denture base polymer guide to dental materials and devices, 7th edition, Chicago Illinois.
- Alhavaz, A., Rezaei Dastjerdi, M., Ghasemi, A., Ghasemi, A., & Alizadeh Sahraei, A. (2017). Effect of untreated zirconium oxide nanofiller on the flexural strength and surface hardness of autopolymerized interim fixed restoration resins. *Journal of esthetic and restorative dentistry : official publication of the American Academy of Esthetic Dentistry ... [et al.]*, 29(4), 264–269.
<https://doi.org/10.1111/jerd.12300>

- Al-Harbi, F. A., Abdel-Halim, M. S., Gad, M. M., Fouda, S. M., Baba, N. Z., AlRumaih, H. S., & Akhtar, S. (2019). Effect of Nanodiamond Addition on Flexural Strength, Impact Strength, and Surface Roughness of PMMA Denture Base. *Journal of prosthodontics: official journal of the American College of Prosthodontists*, 28(1), e417–e425. <https://doi.org/10.1111/jopr.12969>
- Al-Hiloh, S. A., & Ismail, I. J. (2016). A Study the Effect of Addition of Silanized Zirconium Oxide Nanoparticles on Some Properties of High-Impact Heat-Cured Acrylic Resin. *Journal of Baghdad College of Dentistry*, 28(2), 19–25. <https://doi.org/10.12816/0028208>.
- Al-Judy, H. J., Ahmed, A. N., & Abdul-Razak, R. W. (2016). Evaluation of Impact and Transverse Strength of Denture Bases Repaired with Nano Reinforced Resin. *Journal of Baghdad College of Dentistry*, 28(4), 9–15. <https://doi.org/10.12816/0033204>
- Al-Sammraie, M. F., Fatalla, A. A., & Atarchi, Z. R. (2024). Assessment of the correlation between the tensile and diametrical compression strengths of 3D-printed denture base resin reinforced with ZrO₂ nanoparticles. *Journal of Baghdad College of Dentistry*, 36(1), 44–53. <https://doi.org/10.26477/jbcd.v36i1.3590>
- Ayad N.M., Badawi M.F., Fatah A.A. (2008). Effect of reinforcement of high impact acrylic resin with micro-Zirconia on some physical and mechanical properties. *Rev. Clinical. Dental.*; 4(2): P 145-151.
- Chladek, G., Pakielą, K., Pakielą, W., Żmudzki, J., Adamiak, M., & Krawczyk, C. (2019). Effect of Antibacterial Silver-Releasing Filler on the Physicochemical Properties of Poly(Methyl Methacrylate) Denture Base Material. *Materials (Basel, Switzerland)*, 12(24), 4146. <https://doi.org/10.3390/ma12244146>.
- Choksi, R. H., & Mody, P. V. (2016). Flexural properties and impact strength of denture base resins reinforced with micronized glass flakes. *Journal of Indian Prosthodontic Society*, 16(3), 264–270. <https://doi.org/10.4103/0972-4052.176532>.
- Ellakwa, A. E., Morsy, M. A., & El-Sheikh, A. M. (2008). Effect of aluminum oxide addition on the flexural strength and thermal diffusivity of heat-polymerized acrylic resin. *Journal of prosthodontics: official journal of the American College of Prosthodontists*, 17(6), 439–444. <https://doi.org/10.1111/j.1532-849X.2008.00318.x>
- Fareed Al-Sammraie, M., A Fatalla, A. (2023). 'The Effect of ZrO₂ Nanoparticles Addition on Candida Adherence and Tensile Strength of 3D Printed Denture Base Resin', *Journal of Nanostructures*, 13(2), pp. 544-552. doi: 10.22052/JNS.2023.02.024
- Gad, M. M., Abualsaud, R., Rahoma, A., Al-Thobity, A. M., Al-Abidi, K. S., & Akhtar, S. (2018). Effect of zirconium oxide nanoparticles addition on the optical and tensile properties of polymethyl methacrylate denture base material. *International journal of nanomedicine*, 13, 283–292. <https://doi.org/10.2147/IJN.S152571>
- Hasen K.S, Naji GA, JaburRK.(2023). Enhancing Surface roughness and Wettability of Commercial Pure Titanium Implants with Electrospun PCL/Chitosan/Cinnamon composite. *Misan journal of academic studies*
- Hussein, N. A., & Ali, N. A. (2022). Synthesis and Characterization of Ni₂O₃ as a Phase of Nickel Oxide Nanomaterial. *Iraqi Journal of Science*, 4733–4739. <https://doi.org/10.24996/ijs.2022.63.11.12>

- Ismiyati, T., & Alhasyimi, A. A. (2023). Effect of Chitosan and Acrylic Acid Addition to Acrylic Resin on Porosity and Streptococcus mutans Growth in Denture Base. *European journal of dentistry*, 17(3), 693–698. <https://doi.org/10.1055/s-0042-1751002>
- International Standard Organization: plastic determination of Charpy impact strength of rigid materials. ISO179 (2000).
- Jagger, D. C., Harrison, A., & Jandt, K. D. (1999). The reinforcement of dentures. *Journal of oral rehabilitation*, 26(3), 185–194. <https://doi.org/10.1046/j.1365-2842.1999.00375.x>
- J. A. Kenneth, C. Shen, and H. R. Rawls, (2013). Phillips' Science of Dental Materials, Elsevier Saunders, Philadelphia, Pa, USA, 12th edition.
- Karci, M., Demir, N., & Yazman, S. (2019). Evaluation of Flexural Strength of Different Denture Base Materials Reinforced with Different Nanoparticles. *Journal of prosthodontics: official journal of the American College of Prosthodontists*, 28(5), 572–579. <https://doi.org/10.1111/jopr.12974>
- Khairi, A., & Naji, G.-H. (2023). The effect of silica nano particle derived from natural rice on surface roughness and wettability of high impact heat cure resin. *Medical Journal of Babylon*, 20(2), 308. https://doi.org/10.4103/mjbl.mjbl_346_22.
- Kong, M., Chen, X. G., Xing, K., & Park, H. J. (2010). Antimicrobial properties of chitosan and mode of action: a state of the art review. *International journal of food microbiology*, 144(1), 51–63. <https://doi.org/10.1016/j.ijfoodmicro.2010.09.012>
- Leão, R. S., Moraes, S. L. D., Gomes, J. M. L., Lemos, C. A. A., Casado, B. G. D. S., Vasconcelos, B. C. D. E., & Pellizzer, E. P. (2020). Influence of addition of zirconia on PMMA: A systematic review. *Materials science & engineering. C, Materials for biological applications*, 106, 110292. <https://doi.org/10.1016/j.msec.2019.110292>
- MAH, B., & Aljafery, A. M. (2015). Effect of Addition ZrO₂-Al₂O₃ Nanoparticles Mixture on Some Properties and Denture Base Adaptation of Heat Cured Acrylic Resin Denture Base Material. *Journal of Baghdad College of Dentistry*, 27(3), 15–21. <https://doi.org/10.12816/0015028>.
- Maitra, U., Prasad, K. E., Ramamurty, U., & Rao, C. N. R. (2009). Mechanical properties of nanodiamond-reinforced polymer-matrix composites. *Solid State Communications*, 149(39–40), 1693–1697. <https://doi.org/10.1016/j.ssc.2009.06.017>
- Protopapa, P., Kontonasaki, E., Bikiaris, D., Paraskevopoulos, K. M., & Koidis, P. (2011). Reinforcement of a PMMA resin for fixed interim prostheses with nanodiamonds. *Dental materials journal*, 30(2), 222–231. <https://doi.org/10.4012/dmj.2010-135>
- Rasan, D., & Farhan, F. (2023). Effect of addition of polymerized polymethyl methacrylate (PMMA) and zirconia particles on impact strength, surface hardness, and roughness of heat cure PMMA: An in vitro study. *Dental Hypotheses*, 14(1), 36. https://doi.org/10.4103/denthyp.denthyp_151_22.
- Vojdani M. and Khaledi A. A. R., (2006). Transverse Strength of Reinforced Denture Base Resin with Metal Wire and E-Glass Fibers. *Journal of Dentistry*; 3(4): P 167-172.