

**Tareq S. al-Attar** 

Building and Construction  
Engineering Department,  
University of Technology  
Baghdad, Iraq  
[40076@uotechnology.edu.iq](mailto:40076@uotechnology.edu.iq)

**Ahmed A. Taha**

Building and Construction  
Engineering Department  
Baghdad, Iraq

Received on: 13/03/2017  
Accepted on: 11/01/2018  
Published online: 25/12/2018

## Resistance of High-Volume Fly Ash Self-Compacting Concrete to Internal Sulfate Attack

**Abstract-** This paper investigates the durability of high-volume Fly ash self-compacting concrete, HVFASCC that exposed to internal sulfate attack. At the present work, HVFASCC was produced with two Fly ash replacements: 50 and 60% by weight of Portland cement. The internal sulfate attack was simulated by adding natural gypsum ( $\text{CaSO}_4$ ) that contain ion ( $\text{SO}_3^{2-}$ ) to fine aggregate by two weight percentages: 1 and 2%. Limestone dust was used as filler with a content of  $100 \text{ kg/m}^3$ . The cementitious materials, cement and Fly ash, content was  $400 \text{ kg/m}^3$  and the water to powder ratio for the studied mixes was 0.34 by weight. To ensure the self-compact ability of the mixes, slump flow, T500, V-funnel and L-box tests were done. The Compressive, Splitting and Flexural strength Tests were extended to the age of 240 days. The results showed that there is no significant difference between 1 and 2% of  $\text{SO}_3$  content on the behavior of all mixes. The presence of limestone powder in the paste solution could have a role in stabilizing ettringite and reducing paste porosity at early ages. At later age, 240 days, the harmful effect of  $\text{SO}_3$  is diminished and that may be caused by the depletion of gypsum and the dominant product will be calcium monosulfaluminate hydrates instead of calcium sulfoaluminate hydrates.

**Keywords-** High-volume Fly ash, Limestone, HVFASCC, Strength, Sulfates.

**How to cite this article:** T.S. al-Attar and A.A. Taha, "Resistance of High-volume Fly Ash Self-compacting Concrete to Internal Sulfate Attack," Engineering and Technology Journal, Vol. 36, No. 12, pp. 1260-1266, 2018.

### 1. Introduction

Concrete is the most widely used material in the world. It plays an important role in infrastructure and private buildings construction. Self-compacting concrete, SCC, is special type of concrete which can be placed and compacted under its self-weight without vibration effort, and which has in the same time cohesive enough to be placed without segregation or bleeding. This type of concrete is used to facilitate and ensure proper filling and performance of the good structural of narrow areas and members congested reinforced concrete structure [1].

SCC is used in all elements of all civil engineering construction such as substructures, infrastructure, industrial floors and Installations that are regularly subjected to aggressive environmental condition [2].

The Brundtland Report defined sustainable development as the ability of humanity to ensure that it meets the needs of the present without compromising the ability of future generations to meet their own needs [3].

Three components of sustainability are environment, economy and society. These components must be maintained healthy and balanced simultaneously to keep on the entire of planet now and in the future [4].

Today, the use of Pozzolanic materials, such as Fly ash can reduce the use of manufactured Portland cement, and make concrete more durable [5].

Fly ash reacts with calcium hydroxide, a by-product compound of cement hydration, to produce calcium silicate hydrate, which consider desirable cementations product of cement hydration. This process leads to increase strength at later ages, reduces heat of hydration, and reduces the rate of concrete free shrinkage, resulting in a decrease in thermal shrinkage cracking due to the reduction in cement content. In addition, improves resistance of concrete against sulfate and alkalis-silica reaction and permeability.

[7] Mentioned that internal sulfate attack takes place because of the reaction between sulfates found in concrete ingredients, water, cement,

sand and gravel, with calcium aluminates, C3A, and water to form calcium sulphoaluminate, which causes high tensile stresses, lead to expansion and disruption of concrete.

The more common form of internal sulfate attack is the existence of CaSO<sub>4</sub> that interacts either with C3A or calcium sulphoaluminate, C<sub>6</sub>A<sub>3</sub>H<sub>3</sub>2, with Ca(OH)<sub>2</sub> and water to form ettringite which has the form of hard-rod crystals and large volume lead to generate interior expansion and tensile stress [8].

If the cement was substituted by high-volume mineral admixture, such as Fly ash, the amount of produced ettringite will be reduced and effected by the insufficient portlandite Ca(OH)<sub>2</sub>. The development of expansive will be limited. In additional at the late stage although that CaOH<sub>2</sub> is available in abundant amount but the hydration of mineral admixture need to consume partial of Ca(OH)<sub>2</sub> and the development of expansive effect would be restrained again [8].

Borosnyói [9] stated that durability of concrete is considerably improved by the incorporation of supplementary cementing materials (SCMs). Due to the pozzolanic activity and the filling effect, use of SCMs can produce high performance concrete having both enhanced mechanical characteristics and reduced permeability that leads to improved durability.

Crouch [10] pointed out that using High Volume Fly ASH (HVFA) in concrete gives a wide range of benefits, but the most attractive is durability. It was studied four mixes, two with Fly ash, 25% class C and 20% class F, respectively and two other mixes with HVFA, 50% class C and 50% class F, respectively. The mechanical and physical properties of these mixes were investigated and found that compressive strength for mix with HVFA class C ash gave in early age similar compressive strength to mix with Fly ash 25% but in late age, the strength of HVFA mix was greater. Also regarding class F ash, the mix with HVFA gave lower strength than mix with 20% class F ash in early age but the strength become similar in later age. Regarding the absorption and permeability, the mixes with HVFA had always better results than mixes with lower Fly ash contents in all ages.

This investigation deals with effect the internal sulfates that are presented in fine aggregate on properties of self-compacting concrete containing high-volume Fly ash, 50 and 60 % by weight of cement.

This investigation could be considered as an implementation of sustainability requirements. Using (HVFASCC) with more than 50% replacement of Portland cement will serve sustainability by:

1. Reducing the Portland cement content in concrete is a crucial factor in reducing the CO<sub>2</sub> gas emissions and therefore affects the global warming.
2. Using high quantity of Fly ash, which is a by-product material from electric power plant in many of countries, will enhance the waste management systems in the globe.
3. Making use of Fly ash plays an important role in improving many of properties of concrete and also improves durability that linked to the concept of sustainability.

## 2. Experimental Work

### Materials

#### 1. Cement

Iraqi ordinary Portland cement with commercial name Karasta was used. The test results showed that this cement conforms to requirement of European standard EN 197- 1:2011 [11]. The physical and chemical properties of this cement are given in Tables 1 and 2 respectively.

**Table 1: Physical properties of cement tested by National Center for Structural Laboratories**

No	Physical properties	OPC	Limits of EN 197-1:2011]
1	Specific surface area (Blaine method) m <sup>2</sup> /kg	376	> 230
2	Setting time, hrs: min	2:05	> 45mins
	Initial setting	4:00	≤ 10hrs
	Final setting		
3	Soundness(autoclave method), %	0.12	<0.8
4	Compressive strength ,MPa, at age		
	3 days	20	≥ 15
	7 days	25	≥ 23

\*OPC: Ordinary Portland cement

**Table 2: chemical composition of the cement**

No.	Properties	Test	Test result	Limits of IQS No.5 /1984 for (OPC) [11]
1	Oxide content %	CaO	66.11	-
		SiO <sub>2</sub>	21.93	-
		Al <sub>2</sub> O <sub>3</sub>	4.98	-
		Fe <sub>2</sub> O <sub>3</sub>	3.1	-
		MgO	2.0	<5
		SO <sub>3</sub>	2.25	<2.8
2	Loss on ignition, LOI		2.39	<4
3	Lime saturation factor, IR		0.93	0.66-1.02
4	Insoluble residue, LSF		1.29	<1.5
5	Compound composition (bouge's equation),%	C <sub>3</sub> S	64.57	-
		C <sub>2</sub> S	14.15	-
		C <sub>3</sub> A	7.95	>3.5
		C <sub>4</sub> AF	9.43	-

*II. Fine aggregate*

Al Ukhaider sand from quarries of karbalaa region was used as fine aggregate. The gradation and sulfate content were tested and were conforming to the Iraqi Standard No.45/1984 – Zone 2 [12] as shown in Table 3.

*III. Coarse aggregate*

Crushed natural gravel from Nibaae region locates north of Baghdad (Iraq) with maximum size of 20 mm was used in this work. Table 4 represent list the properties of this aggregate and conformed to requirement of Iraqi slandered.

**Table 3: Properties of fine aggregate**

Sieve size (mm)	Percentage passing	Limits of IQS No.45 /1984 – zone 2
10	100	100
4.75	95	90-100
2.36	79	75-100
1.18	59	55-90
0.6	39	35-59
0.3	15	8-30
0.15	6	0-10
Sulfate content, %	0.103	≤ 0.5
Fine materials passing from sieve (75 μm), %	3.9	≤ 5
Specific gravity, SSD	2.65	-
Fineness modulus %	3.07	-

**Table 4: grading of the coarse aggregate**

Sieve size (mm)	Percentage passing %	Limits of IQS No.45 /1984 (5-20 mm) %
37.5	100	100
20	100	95-100
14	-	-
10	40	30-60
5	10	0-10
2.36	0	-
Sulfate content as a SO <sub>3</sub> %	0.08	0.1
Specific gravity, SSD	2.7	

*IV. Natural gypsum*

Natural gypsum was used from Salah al-Deen region. It was got as a rock, then crushed by hummer and sieved on sieves to gradation to be filled with that of fine aggregate. The percentage of sulfate, as SO<sub>3</sub> in gypsum was 42%. The following equation [13] was adopted in calculating the required quantity of gypsum to be added to the fine aggregate:

$$W = (R-X)S/N \quad \dots (1)$$

Where:

W: the weight of added gypsum, kg.

R: the desired percentage of SO<sub>3</sub>.

X: the actual percentage of SO<sub>3</sub> in fine aggregate (0.1 %).

S: the weight of fine aggregate in the mix, kg.

N: percentage of SO<sub>3</sub> in gypsum (42%).

Gypsum was used as partial replacement by weight of sand by two percentages, 1 and 2%, to simulate the sulfate contamination in natural sand.

*V. Fly ash*

The used Fly ash is meeting the requirements of ASTM C 618 (Class F) [14]. It has a specific surface area of 730 m<sup>2</sup>/kg; the characteristics of Fly ash used herein are presented in Table 5 and 6.

**Table 5: Physical properties of used Fly ash class F**

No	Physical properties	result	Limits of ASTM C 618-03[14]
1	Specific surface area (Blaine method) m <sup>2</sup> /kg	773	-
2	Specific gravity	2.33	-
3	Amount retained when wet-sieved on 45 μm (No. 325) sieve %	15.1	<34
4	Compressive strength activity index,MPa, at age	28 days	
		90 days	84.4 ≥ 75 96.9 ≥ 85

**Table 6: Chemical properties of used Fly ash class F**

parameter	average	Limits of ASTM C 618-03[14]
Loss on ignition %	3.1	≤6
Sulfate(SO3) %	0.4	≤5
Compound composition %	SiO2 65.65	Total ≥ 70%
	Fe2O3 5.98	
	Al2O3 17.69	
	MgO 0.72	-
	CaO 0.96	-
	Na2O 1.35	-
	K2O 2.99	-

*VI. Limestone powder*

In this work, crushed limestone brought from local market is used and the fineness of the gained material is (239 m<sup>2</sup>/kg).The average particle size of the limestone powder according EFNARC requirement[15] may be less than 0.125mm to achieve its most benefits. The limestone powder passing sieve No. 0.125 mm is used in this work. The fine limestone powder (commercially named as Al-Gubra) was from of Al Anbar region.

**Table 7: Chemical Analysis of the Limestone Powder**

No.	test	result
1	SO3 percent	0.77
2	Specific surface area (Blaine method) m <sup>2</sup> /kg	239
3	Compound composition %	CaO 56.1
		SiO2 1.38
		Fe2O3 0.12
		Al2O3 0.72
		MgO 0.13
	L.O.I	4.56

*VII. High – range water-reducing admixture (super plasticizer)*

A high –range water reducing admixture, the commercial name is GLENIUM 54 from BASF Company was used in mixes. It is a third generation of super plasticizer those based on sulphonated melamine and naphthalene.it is based on a unique carboxylic ether polymer with a long lateral chains. It has relative density of 1.07 kg/l at 20°C according to brochure of company. The normal dosage for GLENIUM 54 is between 0.5 and 1.6 lit/100kg of cement (cementitious material) and dosage outside this range is permissible and is subjected to trail mixes. It was found that the optimum dosage is 1.1 - 1.35 lit/100kg of cement and Fly ash contents.

*Experimental program*

Two mixes (R50 and R60) were used as references in this work, to achieve 30MPa as characteristic compressive strength at 28 days for (100\*100\*100 mm) cubes depending on reference [15]. The powder content was 500 kg/m<sup>3</sup> and the water to powder, (W/P), ratio is 0.34 by weight (Table 8):

1. Mix R50 with 50% Fly ash replacement by weight of cement.
2. Mix R60 with 60% Fly ash replacement by weight of cement.

The R50 mix was reproduced as mixes R50S1 and R50S2 with two sulfate contents of sand, 1 and 2% respectively and the same was done with mix R60 to produce R60S1 and R60S2. Therefore, the total number of mixes was six. All these mixes were water-cured till the age of test.

**Table 8: The details of the reference mixes**

Type of mixes	powder material content	Aggregate	Water Kg/ m3	w/powder ratio (W/P)	Super plasticizer l / m <sup>3</sup>	
	Cement Kg/m3	Fly ash Kg/m3	Limestone powder	F.A.* Kg/m3	C.A.** Kg/m3	
Reference Fly ash 50%	200	200	100	840	800	170 0.34 5.25
Reference Fly ash 60%	160	24	100	840	800	170 0.34 5.4

\* F.A.: Fine Aggregate

\*\* C.A.: Coarse Aggregate

**Testing Program**

**Fresh state tests**

To verify SCC fresh characteristics, the following tests were carried out according to the methods that are given in the Guidelines of EFNARC [16]:

1. Slump flow and T50cm.
2. V-funnel and V-funnel at T5minutes.
3. L-box.

**Hardened state tests**


Table 9 lists the conducted tests, the adopted standards, types and dimensions of tested




the same age due to the fact that decreasing cement content in mix R60 would decrease the production of  $\text{Ca(OH)}_2$  which is needed for the Fly ash to react with and building new C-S-H gel [6].

The effect of  $\text{SO}_3$  content in fine aggregate on compressive strength development is shown in Figures 1 and 2 for the studied mixes. It could be observed that there is no significant difference between 1 and 2% of  $\text{SO}_3$  content on the behavior of all mixes. On the other hand, increasing the  $\text{SO}_3$  from 0.1 to 1% has caused a reliable drop in the compressive strength especially at intermediate ages, 28, 90 and 180 days. At early age, 14 days, the reduction in strength is very little and that could be attributed to the long setting time of concrete that resulted from using high contents of Fly ash. The delayed setting makes the paste more flexible to accommodate expected expansions. In addition to that, the presence of limestone powder in the paste solution could have a role in stabilizing ettringite and reducing paste porosity [20].

At later age, 240 days, the harmful effect of  $\text{SO}_3$  is diminished and that may be caused by the depletion of gypsum and the dominant product will be calcium monosulfaluminate hydrates instead of calcium sulfoaluminate hydrates [21]. For the studied mixes, the development of splitting tensile and flexural strengths was similar to that of compressive strength.

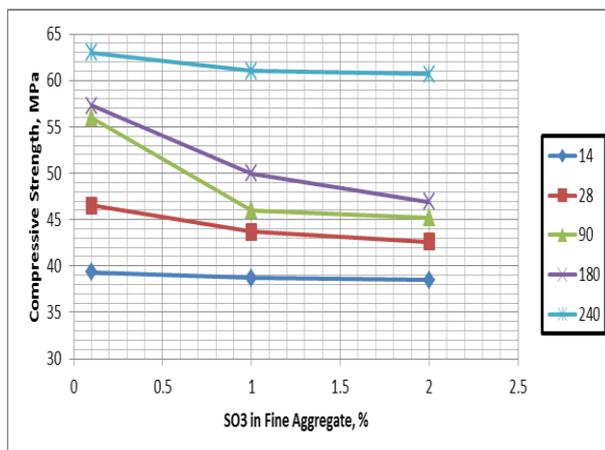

**Figure 1: The effect of  $\text{SO}_3$  content in fine aggregate on the development of compressive strength through days (14, 28, 90, 180, and 240 day) for mixes R50, R50S1 and R50S2.**

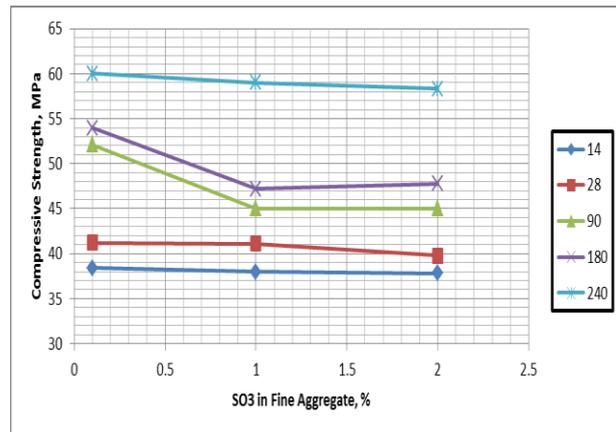

**Figure 2: The effect of  $\text{SO}_3$  content in fine aggregate on the development of compressive strength through days (14, 28, 90, 180, and 240 day) for mixes R60, R60S1 and R60S2**

## Conclusions

The following conclusions could be drawn based on the present experimental results:

1. A self-compacting concrete could be produced by high-volume replacements of Portland cement by Fly ash. At the present work the replacements were 50 and 60% by weight of Portland cement and yet the fresh state tests of the studied HVFASCC mixes were conforming to the requirements of the international standards.
2. There is no significant difference between 1 and 2% of  $\text{SO}_3$  content on which behavior of all mixes.
3. At early age, 14 days, the reduction in strength is zero and that could be attributed to the long setting time of concrete due to replacement by high contents of Fly ash. The delayed setting makes the paste more flexible to accommodate expected expansions.
4. The presence of limestone powder in the paste solution could have a role in stabilizing ettringite and reducing paste porosity at early ages.
5. At later age, 240 days, the harmful effect of  $\text{SO}_3$  is diminished and that may be caused by the depletion of gypsum and the dominant product will be calcium monosulfaluminate hydrates instead of calcium sulfoaluminate hydrates.

## References

- [1] N. Bouzoubaa and M. Lachemi, "Self-compacting concrete incorporating high volumes of class F fly ash Preliminary results," *Cement and Concrete Research*. 31, pp. 413-420, 2001.
- [2] M.T. Bassuoni and M.L. Nehdi, "Durability of self-consolidating concrete to sulfate attack under combined cyclic environments and flexural loading," *Cement and Concrete Research*. 39, pp. 206-226, 2009.

- [3] C. Griffin, "Sustainability, Performance and Mix Design of High Volume Fly Ash Concrete," Individual Research, Prof. Claudia Ostertag, May, California, 2005.
- [4] L. Struble and J. Godfrey, "How Sustainable is Concrete?," Proceedings of the International Workshop on Sustainable Development and Concrete Technology May, China, 2005.
- [5] T.R. Naik and G. Moriconi, "Environmental-friendly durable concrete made with recycled materials for sustainable concrete construction," *Research Gate*. [Online] the TRIS and ITRD database. Available <https://www.researchgate.net/publication/238096274>. [Accessed: 07th February 2014]
- [6] D. Corr and S. Shah, "Design and Application of High Volume Fly Ash Self Consolidating Concrete with the Incorporation of Nanoparticles," *TRD*. [Online]. Available <http://iti.northwestern.edu/publications/utc/safetea-lu/FR-5-CorrShah.pdf>. [Accessed: 2012] FINAL REPORT, 90 p.
- [7] T.S. al-Attar, "Behavior of High Performance Concrete Exposed to Internal Sulfate Attack (Gypsum-Contaminated Aggregate)," *Earth & Space* 2006.
- [8] G. Zhang and G. Li, "Construction and Building Materials," *Construction and Building Material*, 113, pp. 970–978, 2013.
- [9] Borosnyói, "Long term durability performance and mechanical properties of high performance concretes with combined use of supplementary cementing materials," *Construction and Building Materials*, 112, pp.307–324, 2016.
- [10] L.K. Crouch, "High Volume Fly Ash Concrete," *World of Coal Ash (WOCA)*, pp. 1-14, 2007.
- [11] European standards. EN 197-1. "Cement Composition, specification and conformity criteria for common cements," 2011.
- [12] Republic of Iraqi Standard Specification No. (45) of 1984 "Aggregate of Natural Resources Used in Concrete and Construction," Central agency of Standardization and Quality Control, 1984.
- [13] T.K. Al-Kadimi and F. Abood, "Effect of gypsum present in sand on the properties of concrete," *BRC journal*, pp. 17-41, 1983.
- [14] ASTM C 618, "Standard Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use in Concrete," *Annual Book of ASTM Standards*, Vol 04.02, 2013.
- [15] S. Afiniwala, I. Patel and N. Patel, "Effect of High Volume Fly ash on Rheological Properties of Self Compacting Concrete," *International Journal of Emerging Technology and Advanced Engineering*, 3, Issue 7, pp. 1-7, 2013.
- [16] EFNARC, "Specification and Guidelines for Self-Compacting Concrete," Association House, 2002.
- [17] BS EN 12390-3, "Method for determination of compressive strength of concrete cubes," 2003.
- [18] ASTM C 496, "Standard Test Method for Splitting Tensile Strength for Cylindrical Concrete specimens," *Annual Book of ASTM Standards*, 2013.
- [19] ASTM C 78, "Standard Test Method for Flexural Strength Concrete," *Annual Book of ASTM Standards*, Vol. 04, (02), 2013.
- [20] K. De Weerd, "Hydration mechanisms of ternary Portland cements containing limestone powder and fly ash," *Cement and Concrete Research*, 41, pp. 279–291, 2011.
- [21] P.C. Hewlett, *Lea's Chemistry of Cement and Concrete*, 4th Ed. London: Elsevier Science & Technology Books, 2004.

### Authors' biography



**Dr. Tareq S. al-Attar** was born in Baghdad, Iraq in 1960. He is now a Professor of Civil Engineering (Construction Materials Engineering) at the University of Technology, Iraq. He received his BSc of Civil Engineering in 1982 and MSc (Construction Materials Engineering) in 1989 from the University of Baghdad; his PhD in 2001 from the University of Technology, Iraq. His research interests include time-dependent deformations of concrete, durability and sustainability of concrete, high performance concrete and self-compacting concrete. He is currently a member in the American Concrete Institute, ACI since 2005 and joining the ACI Committees 130, Sustainability of Concrete and 209, Creep and Shrinkage of Concrete. In addition, he is a member of the Board of Directors of the ACI Iraq Chapter.



**Ahmed Abdul-Lateef Taha** received his BSc in Construction Engineering from the University of Technology in 2003, MSc in Building Materials Engineering from the University of Technology in 2017, Iraq. His research interests include durability and sustainability of concrete.